

Electrochemical and Adsorption Behaviour of *Diospyros mespiliformis* on Annealed Carbon steel Corrosion in Hydrochloric Acid

R.S. Oguike^{1,2*}, A.M. Kolo¹, A.A. Ayuk², F.C. Eze², E.E. Oguzie²
oguike.rafael@yahoo.com

¹Corrosion Protection and Materials Science Laboratory, Department of Chemistry, Abubakar Tafawa Balewa University, Bauchi, Nigeria

²Electrochemistry and Materials Science Research Laboratory, Department of Chemistry, Federal University of Technology, Owerri, Nigeria

Abstract

The interfacial activities of *Diospyros mespiliformis* on annealed carbon steel in 2 M HCl solution was studied by electrochemical methods; polarization and impedance spectroscopy measurements, while weight loss of the carbon steel at varying temperatures and gasometric method was studied. The results of the study revealed that *D. mespiliformis* mitigates the corrosion of carbon steel (FE164531) in HCl solution through adsorption. Results from Tafel plots suggest that *Diospyros mespiliformis* (DM) behaves predominantly as a cathodic inhibitor with highest inhibition efficiency (91%) at 1000 ppm. The Nyquist and Bode plots of the test solutions were similar in both inhibited and free medium and contained capacitive and inductive loops. Thermodynamic parameters suggest that *D. mespiliformis* is adsorbed on carbon steel mainly by physical adsorption. The values of enthalpy and entropy of adsorption suggests that DM adsorption on FE164531 surface was spontaneous. A good correlation was obtained following the percentage inhibition efficiencies calculated from all the techniques employed.

Key words: Annealed carbon steel, *Diospyros mespiliformis*, corrosion inhibition, adsorption, Hydrochloric acid

1. INTRODUCTION

The significance of corrosion protection of carbon steel in acidic solutions has become necessary due to its propensity to be attacked in acidic media when deployed in services like acid pickling, chemical cleaning of scale in metallurgy, electrochemical systems, oil recovery and also the petrochemical industry. The protection of carbon steel against corrosion in acidic environments can be achieved in various ways using corrosion inhibitors [1-3]. Several research have been carried out on the use of eco-friendly inhibitors to contain corrosion of carbon steel, mild steel, stainless steel, aluminium and many other metals in both acid and alkaline solutions [4-7]. Corrosion inhibitors are commonly added in small quantity to pickling acids, acid stimulation fluids, cooling waters, oil and gas production streams, either continuously or intermittently to control attacks. These inhibitors generally control corrosion by forming various types of films either by adsorption or the formation of bulky precipitates, and/or the formation of a passive layer on the metal surface that modify corrosivity [8-10]. The mechanism of most corrosion inhibitor on metal oxidization can be explained on the basis of molecular adsorption, which involves forming a thin, invisible film that coat the metal thereby protecting it from attack or a combination of adsorption films and corrosion product forms a passive layer on the metal surface [11]. In aqueous acidic solutions, corrosion inhibitors subsist either as neutral molecules or protonated molecules which adsorb on the metal/acid solution interface through electrostatic attraction between charged molecules and charged metal or by the interaction of unshared π electrons in the inhibitor molecule with the metal surface [12]. Apart from sea water, hydrochloric acid remains the main source of the aggressive chloride ions in aqueous solutions and occurrences of carbon steel corrosion in environments containing chloride ions are known [13]. Several reports claimed the used of green inhibitor as cheap, effective, renewable and non-

toxic for metal corrosion [14-20]. The effectiveness of these bio-extracts as metal corrosion inhibitor mainly depend on its phytochemical functional groups having; steric effects, π -orbital character of donating electrons via adsorption at active sites and electronic density of donor atoms among other variables. *Diospyros mespiliformis* commonly called African ebony is confined to tropical and sub-tropical regions notably in Central and West Africa [21]. Several ethnopharmacological applications have been reported for *D. mespiliformis* which include the use of leaves decoction as extraordinary remedy for fever, whooping cough and for wounds [22,23]. GC-MS analysis of extracts from *Diospyros mespiliformis* yielded components such as triterpenes, carotenoids, saponosides, anthracenosides, anthocyanosides and tannins [21].

In this present work, corrosion study was made using annealed carbon steel immersed in aerated stagnant 2 M HCl solutions with and without addition of ethanolic extract of *D. mespiliformis* leaves, using weight loss, gasometry and electrochemical techniques. The corrosion rate (mpy) of carbon steel and inhibition efficiency of *D. mespiliformis* leaves extract was evaluated with the different methods employed while insight into the adsorption mechanism was assessed through electrochemical impedance spectroscopy (EIS). The experimental data were fitted into Langmuir adsorption isotherm while the effects of temperature gave thermodynamic parameters such as ΔH_{ads} and ΔS_{ads} .

2. EXPERIMENTAL

2.1 Material preparation

Corrosive solutions were freshly prepared from analytical grade chemical reagents using bidistilled water and were used without further purification for each test run. Annealed carbon steel (FE164531) sheets of 99.5% purity, used for this study has the following typical analysis

ppm: C< 1200, Mn< 5000, S< 500, P< 500 which was procured commercially from Advent research materials Ltd, Eynsham Oxford England OX29 4JA. The sheet was mechanically press-cut into 40 x 40 x 0.92 mm coupons with a hole of 1mm drilled at the middle of the upper edge of the coupons and then polished successively with metallographic emery paper of increasing fineness of up to 1200 grits. These coupons were degreased in absolute ethanol, dried in acetone, further dried with hot air and stored in moisture-free desiccator prior usage. Dried leaves of *D. mespiliformis* were blended to powder form; 10 g of powdered leaves was refluxed in 100 ml ethanol for 3 h, allowed to cool for 6 h and filtered. The filtrate was concentrated using rotary evaporator and stored in an oven at 40 °C. From the concentrate, inhibitor test solutions were prepared in concentrations of 10 ppm, 100 ppm and 1000 ppm.

2.2 Weight loss

In gravimetric measurements, FE164531 coupons were weighed before total immersion in a 250ml beaker containing 200 ml test solutions, being suspended by suitable hooks at 1 cm below the solution surface. The beakers were placed in a freely aerated thermostated water bath maintained at constant temperature at 303, 313, 323 and 333 ± 0.5 K. The coupons were retrieved after 3 hours, scrubbed with brush under running bidistilled water, dried as before and weighed [13]. The difference in weight of the coupons before and after immersion in different test solutions was taken as the weight loss. The corrosion rate of the carbon steel and inhibition efficiency of the inhibitor (E_w %) was calculated using the following equations 1 and 2 respectively [10]

$$CR \text{ (mpy)} = \frac{534 \Delta W}{\rho AT} \quad (1)$$

$$E_W\% = \frac{CR^0 - CR}{CR^0} \quad (2)$$

where ΔW is weight loss in mg, ρ is the density of carbon, A the area of the coupon in inches, T is the immersion time in hours, CR and CR^0 are the corrosion rate in the presence and absence of inhibitors respectively.

103

104 **2.3 Gasometric**

Fifty milliliters of test solutions poured into a reaction vessel was used in the gasometric method. Upon introduction of the metal coupon, the vessel was quickly corked and the initial volumes of air in the burette, taken against that of the paraffin oil were recorded. The decrease in volume of the paraffin oil in the burette due to hydrogen gas evolution was noted after every five minutes till the last volume of paraffin oil in the burette. The volume of hydrogen gas evolved was used to evaluate inhibition efficiency of the test inhibitors using equation 3 [24]

$$E_H\% = 1 - \frac{CR_H}{CR_H^0} \quad (3)$$

where CR_H and CR_H^0 are corrosion rates got from total volume of gas evolved in the presence and absence of test inhibitors respectively.

114

115 **2.4 Polarization technique**

The electrochemical experiments were carried out in a three-electrode electrochemical cylindrical Pyrex glass cell with a graphite rod counter electrode and saturated calomel electrode (SCE) as reference. Annealed carbon steel having an exposed area of 1cm^2 was used as working electrode. Before recording the polarization curves, the working electrode was kept at its open circuit value in aerated stagnant 2 M HCl solution without and with inhibitor for 30 min. All electrochemical experiments were performed at room temperature ($27 \pm 1^\circ\text{C}$) using a VersaSTAT

3 electrochemical System. The potentiodynamic polarization curves were obtained by scanning the potential of working electrode from -0.25 V to 1.7 V vs. SCE at a scan rate of 1 mV/s [8], while impedance spectroscopy experiments (EIS) was scanned at the open-circuit potential at frequencies from 100 kHz to 0.1 Hz with AC signal amplitude of 5 mV peak-to-peak along phase shifts between AC voltage and current. The Nyquist and bode plots were acquired using ZSimpWin Version 3.20. The values of E_{corr} , i_{corr} , R_t and C_{dl} were obtained from the electrochemical measurements. The inhibition efficiencies were determined using equations below:

$$E_i \% = \frac{i_{corr}^{\circ} - i_{corr}}{i_{corr}^{\circ}} \quad (4)$$

$$E_R \% = 1 - \frac{R_{ct}^0}{R_{ct}} \times 100 \quad (5)$$

Where i_{corr} and i_{corr}° is corrosion current densities for inhibited and uninhibited solutions respectively, while R_t and R_t^0 is charge transfer resistance in the presence and absence of inhibitor molecules respectively.



3. RESULTS AND DISCUSSIONS

3.1 Polarization measurements

Figure 1 shows the anodic and cathodic polarization curves for FE164531 while calculated electrochemical parameters such as, corrosion potential (E_{corr}), corrosion current density (i_{corr}), degree of surface coverage of the inhibitor (θ), the inhibition efficiency of the inhibitor (E_i %) and linear polarization resistance (R_p) values are listed in Table 1. As can be seen from Fig. 1, the polarization curves showed features of spontaneous passivation in all test media. Addition of *D. mespiliiformis* leaves extracts at varying concentrations did not visibly alter the polarization

145 behavior of the metal in the active metal dissolution region at the anode but however, a decrease
146 in current density was observed. This suggests that *D. mespiliformis* did not interfere with the
147 corrosion mechanism of FE164531 carbon steel, however the inhibitor additives caused a
148 decrease in both cathodic and anodic currents proposing a reduction in anodic dissolution and
149 retardation of hydrogen evolution reaction [5,8]. The cathodic polarization curves exhibit active
150 behaviour with increasing inhibitor concentration with a shift towards lower current density
151 region. The anodic polarization curves are almost identical irrespective of the concentration of
152 test inhibitor. The lower values of corrosion current density facilitate slow electron transfer in the
153 redox process, hence the rate of corrosion reaction becomes reduced. The decrease of current
154 density indicate the fact that *D. mespiliformis* molecules gets adsorbed on pure carbon steel
155 surface and hence retards the corrosion reaction of electrode with concurrent replacement of
156 electrolyte solution at the metal/electrolyte interface [25]. Figure 1 also reveal a decrease in both
157 corrosion current and potential in the cathodic region with a cathodic shift was observed in the
158 E_{corr} indicating that *D. mespiliformis* is a probable cathodic inhibitor. A spontaneous passivation
159 in the anodic region was seen with a decrease in the corrosion potential as the inhibitor was
160 introduced. This decrease is observed at the initial anodic – active dissolution of FE164531
161 which is an indication of the stability of the film formation comprising of $\gamma\text{-Fe}_2\text{O}_3/\text{Fe}_3\text{O}_4$ on
162 FE164531 surface [3,26]. As the potential becomes more passive, the rates of anodic reactions
163 increase while that of cathodic reactions decreases. This observation is an indication that the
164 formation of $\gamma\text{-Fe}_2\text{O}_3/\text{Fe}_3\text{O}_4$ films gradually spreading over the surface of FE164531. Usually a
165 low current density and long anodization time present a very good protection against corrosion
166 due to the diminution of the porosity of the anodic films formed. The corrosion reaction of

carbon steel in solutions containing chloride ions occur via these mechanisms as reported by Sherif (2012) [27];



The mechanism show that the film formed on the carbon steel surface is a mixed porous film of a precipitated ferrous chloride, FeCl_2 and ferric chloride, FeCl_3 compounds. Considering concentration gradients, the ferrous and ferric chloride specie at metal/electrolyte interface diffuse through the porous film and the diffusion boundary layer and then into the bulk solution through convection currents. This results in continuous uniform and pitting corrosion of FE164531 by attack of the chloride ions. The introduction of inhibitor molecules controlled the corrosion current with a maximum of 91% inhibition efficiency at 1000 ppm concentration. This can be explained on the bases that *D. mespiliformis* at this concentration strongly inhibit and block the corrosion sites on the carbon steel surface and retards uniform corrosion and prevents formation of pits. Table 1 shows that the corrosion potential exhibiting a decrease with increasing concentration could be attributed to the passage of metal ions through the adsorbed film occuring slowly and the corrosion current due to metal ion transportation becoming reduced.

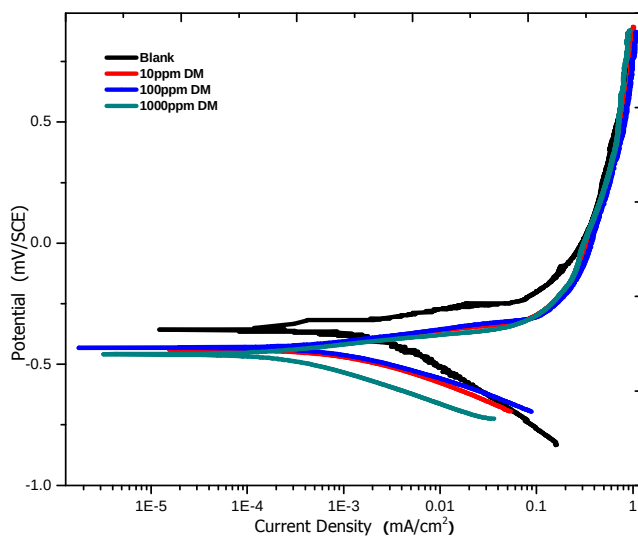


Fig. 1 Anodic and cathodic polarization curves for FE164531 electrode in aerated solution of 2 M HCl in the absence and presence of different concentrations of *D. mespiliformis* leaves extracts.

The inhibition efficiency results of the inhibitor were calculated from the corrosion current (i_{corr}) values according to equation 4 and the values are presented in Table 1. The linear polarization resistance (R_p) was found to increase from 0.496 to 1.497 Ω which results in increase in corrosion current resistance on addition of *D. mespiliformis* to 2 M HCl. On increasing the inhibitor concentration, E_{corr} values were shifted more negative. This proposes that *D. mespiliformis* behaves predominantly as cathodic inhibitor. The increase of polarization resistance with increasing inhibitor concentration is mainly due to its adsorption on FE164531 surface. The value of R_p is a measure of electron transfer across the surface and it increases with an increase in corrosion rate. The values of R_p in Table 1 showed a steady increase following increased inhibitor concentration from 10 ppm to 1000 ppm. This increase as compared to the

blank value indicates a reduction in FE164531 carbon steel corrosion rate through the formation of adsorbed protective film against corrosion attack at the metal/electrolyte interface [28,29].

Table 1 Corrosion parameters obtained from polarization curves for FE164531 carbon steel in 2 M HCl solution in the absence and presence of *D. mespiliformis* leaves extracts.

Solution	Parameters				
	i_{corr} ($\mu\text{A cm}^{-2}$)	$-E_{corr}$ (mV vs SCE)	θ	E_i %	R_p (Ω)
blank	5465.8	357.28	--	--	0.496
10 ppm	2715.03	427.01	0.5033	50	1.272
100 ppm	1342.04	436.27	0.7545	76	1.338
1000 ppm	517.01	443.08	0.9054	91	1.497

3.2 Impedance Spectroscopy Measurements

To determine kinetic parameters for electron transfer reactions at the carbon steel/electrolyte interface, electrochemical impedance spectroscopy experiment was carried out at open circuit potential in the absence and presence of *D. mespiliformis*. Typical Nyquist and Bode plots were obtained at the metal/electrolyte interface for all test solutions. Figure 2 shows the Nyquist plot of one capacitive loop exhibiting an extended semicircle in the complex impedance plane both in uninhibited and inhibited solutions, an indication that corrosion rate is controlled by charge transfer resistance. The impedance diagrams obtained were not perfect semicircles, and increases in diameter as inhibitor concentration increases indicating that the presence of inhibitor molecules strengthens the inhibitive film and/or the Faradic processes occurring through defects of this film with increase in *D. mespiliformis* concentration. The impedance data obtained are analyzed by simple equivalent Randles circuit which sufficiently explains EIS data for liquid and steam-treated samples [8,30]. Figure 3 shows typical Randles circuit consisting of solution

resistance R_s in series with a component composed of transfer resistance R_t and parallel film capacitance C_{dl} . The obtained values for the charge transfer resistance and parallel film capacitance are listed in table 2. As seen from table 2 that the value of R_t increases in the concentrations of the inhibitor. Figure 4 shows the Bode plots for FE164531 in 2 M HCl with and without different concentrations of *D. mespiliformis* inhibitor. The capacitance of parallel film (C_{dl}) was calculated from equation 7

$$C_{dl} = \frac{1}{2\pi f_{max} R_{ct}} \quad (10)$$

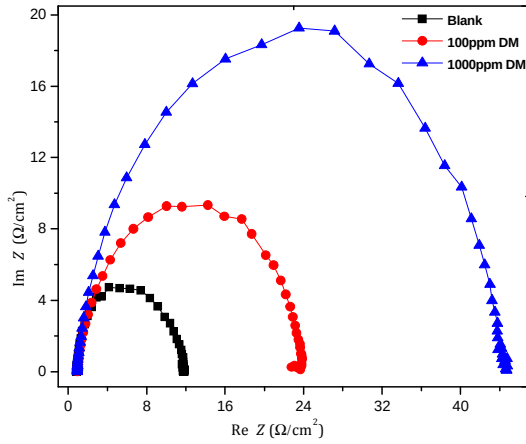


Fig. 2 FE164531 carbon steel in 2 M HCl solutions with and without different concentrations of *D. mespiliformis* leaves extract

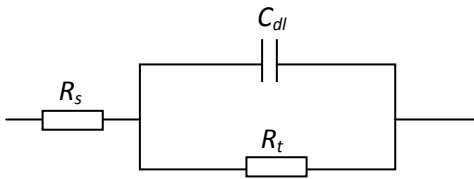


Fig. 3 Electrical equivalent circuit used to fit the impedance data

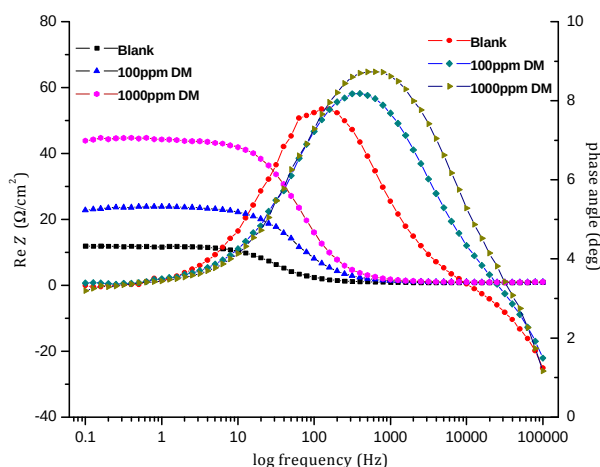


Fig. 4 FE164531 carbon steel in 2 M HCl solutions with and without different concentrations of *D. mespiliformis* leaves extract

Table 2 shows that C_{dl} values decreased when the concentration of the inhibitor molecules increased. The decrease in C_{dl} might arise from a decrease in local dielectric constant and/or an increase of the electrical double layer thickness which might arise from substitution of preadsorbed water molecules on the metal/electrolyte interface by adsorbed organic constituents of *D. mespiliformis* leaves extract whose dielectric constant is lower, suggesting that inhibitor molecules function by adsorption at the metal/solution interface [30].

As the adsorption of the inhibitors at the metal/electrolyte interface increases, there was a gradual decrease in the parallel film capacitance (C_{dl}) and corrosion current values decreased indicating a decrease in local dielectric constant of the electrical double layer [8,31-33]. The inhibitor decreased the C_{dl} values by replacing water molecules present at the electrode surface [34].

The low frequency impedance in the Bode plot continue to increase as the frequency drops, indicating a strong resistance to the flow of ions and electrons through the adsorbed film, hence

preventing corrosion reaction. A capacitive behavior is indicated from medium to low frequencies by phase angles approaching 90° , suggesting that a weak adsorbed film is formed on FE164531 carbon steel in the 2 M HCl solutions which is consistent with physical adsorption.

Table 2 EIS data and adsorption parameters for FE164531 carbon steel in 2 M HCl solutions in the absence and presence of *D. mespiliformis* leaves extract

Solution	Parameters					
	R_t ($\Omega \text{ cm}^{-2}$)	C_{dl} ($\mu \text{ cm}^{-2}$)	θ	E_R %	$-\Delta S$ $\text{Jmol}^{-1}.\text{K}$	ΔH KJmol^{-1}
blank	34.2	294.8	--	--	52.632	44.0076
10 ppm					47.224	45.8647
100 ppm	185.4	104.1	0.8156	82	36.063	49.5686
1000 ppm	267.6	91.7	0.8718	87	16.04	56.3511

3.3 Gasometric technique

The gasometric measurement is based on the idea that the rate of hydrogen gas evolution in a corrosion reaction is directly proportional to the corrosion rate of the metal. This technique, apart from its experimental rapidity, ensures a more sensitive monitoring in situ of any perturbation by the inhibitor vis-a-vis hydrogen gas evolution on the metal-corrodent interphase [24]. The volume of H_2 evolved was observed to appreciably reduce in the presence of test inhibitors as compared to the free acid solution. Further reduction in the volume of H_2 evolved was observed as concentration of test inhibitor molecules increased. Figure 5 reveals that the most remarkable reduction in the volume of H_2 evolved was observed with *D. mespiliformis* molecules at 1000 ppm with inhibition efficiency of the inhibitor at 83 %. The inhibition efficiency of the inhibitor obtained from the hydrogen gas evolution measurements also increased with increase in inhibitor

molecules concentration. The results obtained in the gasometric experiments are in agreement with the trend reported for weight loss and electrochemical measurements [19]. When the surface coverage of the adsorbed inhibitor species increases, lateral reactions between inhibitor molecules may arise, thereby influencing inhibition efficiency. Attractive lateral interactions usually give rise to stronger adsorption hence higher inhibition efficiency [35]. This effect has been shown in cases of compounds containing long chain hydrocarbon because of attractive Van der Waals forces.

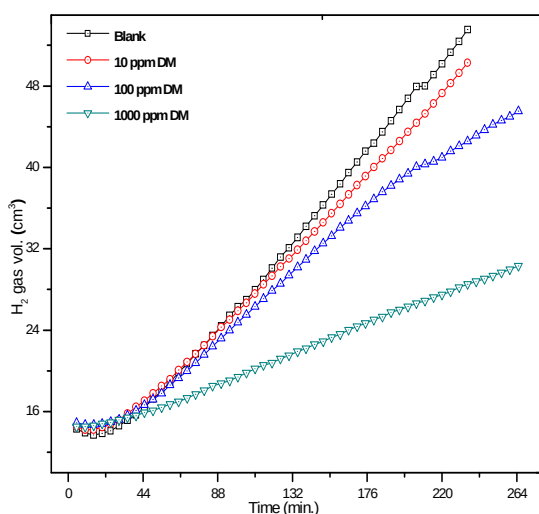


Figure 5 Variation of the volume of H₂ gas evolved with time for FE164531 carbon steel corrosion in 2 M HCl solutions with and without different concentrations of *D. mespiliformis* leaves extract

3.4 Weight loss

FE164531 was found to corrode at an appreciable rate in 2 M HCl solution. Results obtained clearly show that ethanolic extract of *D. mespiliformis* leaves effectively retards corrosion rate of FE164531 carbon steel in 2 M HCl solution, indicating inhibition of the corrosion reaction. The weight loss data reveal the dependence of inhibition efficiency of *D. mespiliformis* on

concentration and temperature. Figure 6 shows variation of FE164531 corrosion rate with temperature in the absence and presence of *D. mespiliformis* molecules. Corrosion rate increased linearly with increase in temperature but decreased with increasing *D. mespiliformis* concentration in the acid solution. Figure 7 shows inhibition efficiency ($E_w\%$) of *D. mespiliformis* leaves extract on FE164531 carbon steel in 2 M HCl solution. It is clear from the figure that increase in concentration of *D. mespiliformis* molecules for all tests performed at varying temperatures result a decrease in corrosion reaction rate indicating geometric blocking effect of *D. mespiliformis* extract at active corrosion sites [36]. The extract inhibits corrosion by controlling the redox reactions. In most of the cases, the nitrogen/oxygen atom present in the inhibitor molecules is easily protonated in acidic solution and converted into quaternary/oxonium ions [37]. These protonated species get adsorbed on the cathodic sites of the metal surface and decrease the hydrogen evolution hence retard metal dissolution. Inhibition efficiency of *D. mespiliformis* leaves extract depends on various factors including but not limited to corrosive strength of the environment, concentration of inhibitor molecules, any synergetic effects with other molecules present in the environment and flow effects [14,38]. Inhibition efficiency trend observed for FE164531 in 2 M HCl using *D. mespiliformis* at varying temperature is an indication of physical adsorption. The evaluated inhibition efficiency had the optimum inhibition efficiency obtained at 68% for 303 K temperature with 1000 ppm inhibitor concentration. The fact that inhibition efficiency decreased with increasing temperature (303 – 313K) signifies that the inhibitors function effectively at lower temperatures. It also indicates that the time lag for the adsorption and desorption of the inhibitor molecules on FE164531 surfaces become shorter at higher temperature.

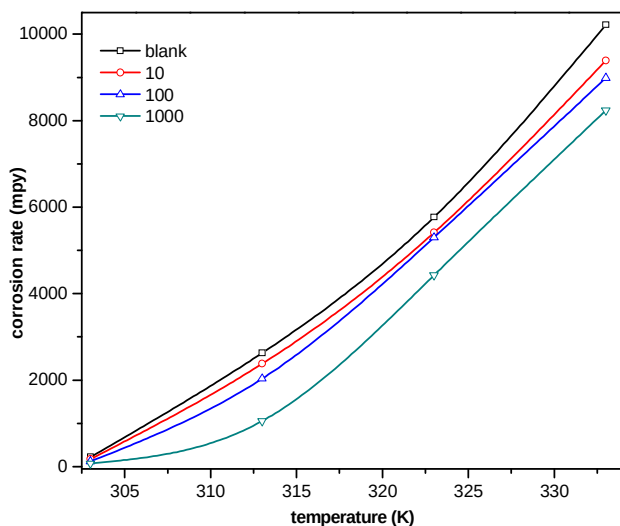


Fig. 6 Linear plot of FE164531 corrosion rate as a function of temperature in the absence and presence of *D. mespiliformis* leaves extract

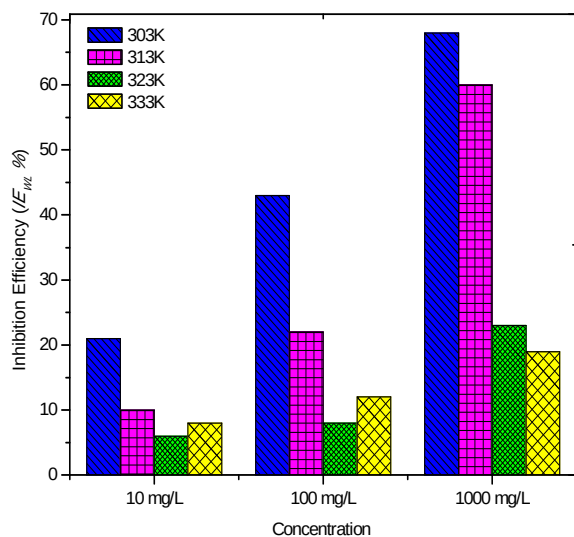


Fig. 7 Inhibition efficiency as a function of *D. mespiliformis* concentration for FE164531 carbon steel in 2 M HCl solutions at varying temperature obtained from weight loss results

3.5 Effect of temperature and adsorption consideration

Temperature investigation allows the determination of thermodynamic functions of annealed carbon steel in 2 M HCl with and without inhibitor. The obtained data were applied Langmuir adsorption isotherm which assumes that percentage area covered by the inhibitor is directly related to decrease in corrosion rate. The Langmuir adsorption isotherm was obtained from equation 11 [14]

$$\log \left(\frac{\theta}{1-\theta} \right) = \log A + \log C - \left(\frac{\Delta H_{ads}}{2.303RT} \right) \quad (11)$$

herein, θ is the surface covered by inhibitor, A the temperature dependant constant, C is the bulk concentration of inhibitor, ΔH_{ads} the heat of adsorption. The heat of adsorption was calculated from slope of the plot of $\log \left(\frac{\theta}{1-\theta} \right)$ vs $1/T$. Figure 8 shows heat of adsorption plot for *D. mespiliformis* on carbon steel in 2 M HCl while ΔH_{ads} values are listed in table 2. It can be observed from the table that inhibitor concentration at 1000 ppm has most positive value and 10 ppm has the least value of heat of adsorption supporting the fact that increase in concentration implies more stabilized adsorbed inhibitor molecule on the surface of FE164531. This could indicate that there was an increase in the adsorbable inhibitors on the metal surface as concentration increased. It is clearly seen in Figure 7 that increase in temperature undermined the integrity of the inhibitor which results to a decrease in inhibition efficiency. This decrease in $E_w\%$ with temperature rise is due to desorption of the inhibitor molecules from the surface of FE164531, thus it can be said that the inhibitor molecules were physically adsorbed on the metal surface. The low positive value of ΔH_{ads} reveal that the process of adsorption of *D. mespiliformis* on carbon steel surface is an endothermic multilayer adsorption process.

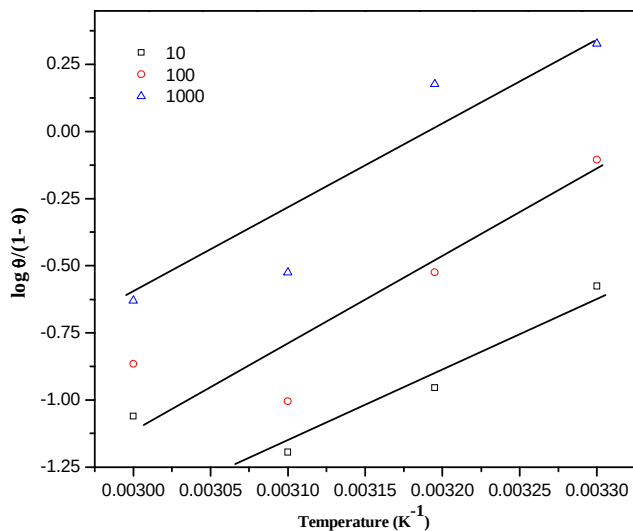


Fig. 8 Heat of adsorption plots as a function of temperature

The adsorption parameters are given in Table 2. The values of ΔH_{ads} increased with increasing inhibitor concentration indicating that the energy barrier of corrosion process increased and the activated complex is higher than that formed in the uninhibited solution. The positive sign of ΔH_{ads} show the endothermic nature of adsorption of *D. mespiliformis* on FE164531 carbon steel surface. The negative values of ΔS_{ads} pointed to a greater order produced during the process of activation. From Table 2, corrosion reaction control could be seen as cooperative effective, that is, ΔH_{ads} and ΔS_{ads} having opposite signs. These two variables could be additive in which the two variables are opposed but the enthalpy values which are larger results an enthalpy-controlled reaction effect [39]. The values of ΔS_{ads} are higher for inhibited solutions than those for the uninhibited solution reflecting an increase in randomness on going from reactants to the activated complex. The increase in values of ΔS_{ads} by the adsorption of *D. mespiliformis* on FE164531 carbon steel surface could be regarded as quasisubstitution between the inhibitors molecules in the aqueous phase and water molecules on electrode surface [40]. However, the

adsorption of *D. mespiliformis* desorbs water molecules from the electrode surface, hence decreasing the surface reactivity of FE164531 carbon steel.

CONCLUSION

The presence of *D. mespiliformis* leaves extract in 2 M HCl solutions for FE164531 carbon steel corrosion inhibition remarkably shifted the values of E_{corr} to the less negative directions and decreased the values of i_{corr} , while the values of R_p increased with increasing inhibitor molecule concentration. This effect is due to the fact that *D. mespiliformis* molecules decrease the severity of HCl solutions and increase the corrosion resistance of FE164531 carbon steel surface by adsorption. The increasing values of IE% obtained with increasing inhibitor concentration is attributed to greater adsorption of inhibitor molecules at active sites on FE164531 carbon steel surface, hence prevention of carbon steel oxides and chlorides formation. This was also confirmed by the agreement between the results gotten from the various methods employed. It is worth noting that the change in the concentration of inhibitor did not alter the profile of the impedance behavior suggesting similar mechanism for the corrosion inhibition of pure carbon steel by inhibitor at various concentrations.

References

1. Chetouani, A., Hammouti, B. and Benkaddour M., Corrosion inhibition of iron in hydrochloric acid solution by jojoba oil. *Pigment Res Technol*, 2004; 33:26-31
2. Sethuraman, M.G. and Raja, P.B., Corrosion inhibition of mild steel by Datura metel in acidic medium, *Pigment Res Technol*, 2005; 34(6): 327–331
3. Ait-Chikh, Z., Chebabe, D., Dermaj, A., Hajjaji, N., Srhiri, A., Montemor, M.F., Ferreira, M.G.S and Bastos, A.C. Electrochemical and Analytical Study of Corrosion Inhibition of Carbon Steel in HCl Medium by 1, 12-bis (1, 2, 4-triazole) dodecane, *Corros. Sci.*. 2005; 47: 447-441
4. Lin Niu, Hu Zhang, Fergus Wei, Suxiang Wu, Xiaoli Cao and Pengpeng Liu. Corrosion Inhibition of Iron in acidic solutions by Alkyl Quaternary Ammonium Halides: Correlation between Inhibition Efficiency and Molecular Structure, *Journal of Applied Surface Science*, 2005; 252(5): 1634-1642
5. El-Etre, A.Y., Abdallah, M. and El-Tantawy, Z.E. Corrosion inhibition of some metals using lawsonia extract, *Corros. Sci.*, 2005; 47(2): 385–395
6. Bothi-Raja, P. and Sethuraman, M.G. Strychnos nux-vomica an eco-friendly corrosion inhibitor for mild steel in 1 M sulfuric acid medium. *Mater. Corros.* 2009; 60: 22-28
7. Abdel-Gaber, A.M., Abd-El-Nabey B.A., and Saadawy M. The role of acid anion on the inhibition of the acidic corrosion of steel by lupine extract. *Corros. Sci.* 2009; 51:1038-1042
8. Arukalam, I.O., Madufor, I.C., Ogbobe, O. and Oguzie, E.E. Acidic Corrosion Inhibition of Copper by Hydroxyethyl Cellulose. *British Journal of Applied Science & Technology* 2014; 4(9): 1445-1460
9. Ekpe, U.J., Ebenso, E.E. and Ibok, U.J. Inhibitory action of *Azadirachta indica* leaves extract on the corrosion of mild steel in H₂SO₄, *J. W. Afri. Sci. Assoc.* 1994; 37: 13-30
10. Oguzie, E.E. Inhibition of acid corrosion of mild steel by Telfaria occidentalis extract. *Pigment & Resin Technology*. 2005; 34(6): 321-326
11. Bouyanzer, A., Majidi, L. and Hammouti, B. Effect of eucalyptus oil on the corrosion of steel in 1M HCl, *Bulletin of Electrochemistry*, 2006; 22(7): 321–324
12. Oguzie, E.E., Iyeh, K.L. and Onuchukwu, A.I. Inhibition of mild steel corrosion in acidic media by aqueous extracts from Garcinia kola seed, *Bulletin of Electrochemistry*, 2006; 22(2): 63–68

13. Oguike, R.S. Corrosion Studies on Stainless Steel (Fe6956) in Hydrochloric Acid Solution. *Advances in Materials Physics and Chemistry*, 2014; 4: 153-163
14. Oguike, R. S., Chindo, I. Y. and Kolo, A. M. Corrosion inhibition and adsorption behaviour of *Parkia biglobosa* on aluminium (AL1043) in acidic media. *Journal of Research in Physical Sciences*, 2013; 9(1): 31 – 41
15. El-Etre, A.Y. Inhibition of C-steel corrosion in acidic solution using the aqueous extract of zallouh root. *Mater. Chem. Phys.* 2008; 108: 278-282
16. Ekpe, U.J., Okafor, P.C. and Ebenso, E.E. Inhibition of the Acid Corrosion of Aluminium by some derivatives of Thiosemicarbazone, *Bulletin of Chemical Society of Ethiopia*, 2004; 18(2): 181-192
17. Oguzie, E.E. Evaluation of the inhibitive effect of some plant extracts on the acid corrosion of mild steel. *Corros. Sci.* 2008; 50: 2993-98
18. Abiola, O.K., Otaigbe, J.O.E., and Kio, O.J. Gossipium hirsutum L. extracts as green corrosion inhibitor for aluminum in NaOH solution. *Corros. Sci.* 2009; 51: 1879-1881
19. Umoren, S.A., Obot, I.B. and Ebenso, E.E. Corrosion inhibition of aluminium using exudate gum from *Pachylobus edulis* in the presence of halide ions in HCl. *E-Journal of Chemistry*, 2008; 5(2): 355–364
20. Eddy, N.O. and Ebenso, E.E. Adsorption and inhibitive properties of ethanol extracts of *Musa sapientum* peels as a green corrosion inhibitor for mild steel in H₂SO₄ *African Journal of Pure and Applied Chemistry*, 2008; 2(6): 46–54
21. Mohamed, I.E., EL-NUR, E.B., Choudhary, M.I. and Khan, S.N. Bioactive natural products from two Sudanese Medicinal plants *Diospyros mespiliformis* and *Croton zambesicus*. *Res. Nat. Prod.* 2009; 3(4): 198-203
22. Palombo, E.A. Phytochemicals from traditional medicinal plants used in the treatment of diarrhea; models of action and effects of intestinal function. *phytotherapy research* 2005; 20: 717-724.
23. Longanga, O.A., Vercruysse, A. and Forriers, A. Contribution to ethnobotanical, phytochemical and pharmacological studies of traditionally used medicinal plants in the treatment of dysentery and diarrhea in Lomelaarea, Democratic republic of congo (DRC) *Journal of ethnopharmacology*. 2000; 71: 411-423

24. Onuchukwu, A.I. The inhibition of aluminium corrosion in an alkaline medium II: Influence of hard bases *Materials Chemistry and Physics*. 1990 : 337–341
25. Khaled, K.F. Corrosion control of copper in nitric acid solutions using some amino acids—A combined experimental theoretical study. *Corros. Sci.* 2010; 52: 3225-3234
26. Khaled, K.F. and Al-Mobarak, N.A. A predictive model for corrosion inhibition of mild steel by thiophene and its derivatives using artificial neural network, *International Journal of Electrochemical Science*, 2012; 7(2): 1045–1059
27. El-Sayed M. Sherif Corrosion Inhibition in Chloride Solutions of Iron by 3-Amino-1,2,4-triazole-5-thiol and 1,1'-Thiocarbonyldiimidazole. *Int. J. Electrochem. Sci.*, 2012; 7: 4834 – 4846
28. Hasanov R, Sadikoglu M, Bilgic S. Electrochemical and quantum chemical studies of some Schiff bases on the corrosion of steel in H₂SO₄ solution. *Appl. Surf. Sci.*, 2007; 253: 3913-3921
29. Gao G, Liang C. Electrochemical and DFT studies of β -amino alcohols as corrosion inhibitors for brass. *Electrochimica Acta*, 2007; 52: 4554-4559
30. F. Bentiss, M. Lebrini, M. Lagrenée, Thermodynamic characterization of metal dissolution and inhibitor adsorption processes in mild steel/2,5-bis(n-thienyl)-1,3,4-thiadiazoles/hydrochloric acid system, *Corros. Sci.* 2005; 47: 2915–2931.
31. H. Amar, A. Tounsi, A. Makayssi, A. Derja, J. Benzakour, A. Outzourhit, Corrosion inhibition of Armco iron by 2-mercaptobenzimidazole in sodium chloride 3% media, *Corros. Sci.* 2007; 49: 2936–2945.
32. X. Li, S. Deng, H. Fu, G. Mu, Inhibition effect of 6-benzylaminopurine on the corrosion of cold rolled steel in H₂SO₄ solution, *Corros. Sci.* 2009; 51: 620–634
33. I. Ahamad, R. Prasad, M.A. Quraishi, Experimental and quantum chemical characterization of the adsorption of some Schiff base compounds of phthaloyl thiocarbohydrazide on the mild steel in acid solutions, *Mater. Chem. Phys.* 2010; 124: 1155–1165
34. N.A. Negm, Y.M. Elkholy, M.K. Zahran, S.M. Tawfik, Corrosion inhibition efficiency and surface activity of benzothiazol-3-ium cationic Schiff base derivatives in hydrochloric acid, *Corros. Sci.* 2010; 52: 3523–3536.

35. Onen, A.I. Determination of the Amount of Corrosion of Iron using different Concentrations of two Alkali Halides with time, *Yedzaram Journal of Science and Technology*, 2000; 1(1): 74-89
36. Oguzie, E.E., Enenebeaku, C.K., Akalezi, C.O., Okoro, S.C., Ayuk A.A., Ejike E.N. Adsorption and corrosion-inhibiting effect of *Dacryodis edulis* extract on low carbon steel corrosion in acidic media. *Journal of Colloid and Interface Science*. 2010; 349: 283-292
37. Ita, B.I. and Edem, C.A. Inhibition of Steel Corrosion in Hydrochloric acid solutions by Green S Erythrosine dyes. *Global Journal of Pure Applied Sciences*, 2000; 60(20): 239-252
38. Gasparac, R. and Martin, C. Investigations of the Mechanism of Corrosion Inhibition by Polyaniline. Polyaniline-Coated Stainless Steel in Sulfuric Acid Solution. *Journal of the Electrochemical Society*, 2001; 148: 4-11
39. N. Surendra Babu Theoretical Study of Stability, Tautomerism, Equilibrium Constants (pKT) of 2-Thiouracil in Gas Phase and Different Solvents (Water and Acetonitrile) by the Density Functional Theory Method *American Chemical Science Journal*. 2013; 3(2): 137-150
40. M.P. Chakravarthy and K.N. Mohana. Adsorption and Corrosion Inhibition Characteristics of Some Nicotinamide Derivatives on Mild Steel in Hydrochloric Acid Solution *ISRN Corrosion* (2014) Article ID 687276, <http://dx.doi.org/10.1155/2014/687276>