

Studies on the Optical and Electrical Properties of 4-methoxybenzoin NLO Single Crystal

Sagadevan Suresh*

Crystal Growth Centre, Anna University, Chennai-25, India.

ABSTRACT

Organic nonlinear optical single crystals of 4-methoxy benzoin were grown by slow evaporation technique. The X-ray diffraction analysis revealed that 4-methoxy benzoin single crystals belong to orthorhombic crystal system with a space group $Pca2_1$. Optical absorption range of the grown crystal was measured by UV-VIS-NIR spectrophotometer. The optical absorbance of 4-methoxy benzoin crystal has been used to calculate the optical band gap (E_g), absorption coefficient (α), refractive index (n), and the real (ϵ_r) and imaginary (ϵ_i) components of the dielectric constant. The DC electrical conductivity measurements were carried out for the crystals using the conventional two – probe technique. The conductivity study indicates that the DC conductivity of the samples increase with the increase in temperature. The activation energies were also calculated from DC conductivity studies. Photoconductivity measurements carried out on the grown crystal reveal the negative photoconducting nature.

Keywords: Solution growth, NLO, Single crystal XRD, UV-VIS-NIR spectra, Refractive index, reflectance, DC electrical conductivity and Photoconductivity studies

1. INTRODUCTION

The growth of optical devices, such as photonic integrated circuitry, depends strongly on the design of extremely efficient nonlinear optical (NLO) materials. Among such NLO materials, organic materials are shown to be superior to their inorganic counterparts in terms of synthesis, crystal fabrication, potential to make large devices and very much faster optical nonlinearities [1] and [2]. Organic derivatives possessing polarizable electrons spread out over a prominent distance with various combinations of terminal electron donor and/or acceptor groups have been the objective of recent research, particularly in view of their large molecular hyperpolarizability and good crystallizability [7-11], which may contribute to a wide range of applications in integrated optics (second harmonic generation (SHG), frequency mixing, electro-optic modulation, parametric effects, etc.) [12, 13]. The design and synthesis of organic molecules exhibiting second-order nonlinear optical (NLO) properties has also been prompted by their enormous potential for application in optical communications, optical computing, data storage, dynamic holography, harmonic generators, frequency mixing and optical switching [10,14]. The synthesis, structural, vibrational, optical and second harmonic generation (SHG) properties of single crystals of 4-methoxy benzoin have been reported earlier [15]. The present investigation, deals with the growth of 4-methoxy benzoin single crystals by slow evaporation technique. The grown single crystals were subjected to single crystal X-ray diffraction, optical absorption, DC electrical conductivity and photoconductivity studies. The results of these investigations are discussed.

* Tel.: 044-22358321; fax: 044-22352774
E-mail sureshsagadevan@yahoo.co.in

2. MATERIAL AND METHODS

Single crystals of 4-methoxy benzoin, an organic nonlinear optical material have been grown by a slow evaporation technique at room temperature. The defect-free, optically clear, and perfectly shaped tiny crystals were chosen as seeds for the growth experiment. From XRD studies, it is confirmed that 4-methoxy benzoin belongs to orthorhombic crystal structure with space group $Pca2_1$. The single crystalline nature is thus confirmed and the space group reveals that the material shows no inversion symmetry (non-centrosymmetric). Optical absorption measurements were made using Perkin Elmer Lambda 35 UV-VIS-NIR spectrophotometer with a resolution of 2 nm in the region from 200 nm to 1000 nm to measure the absorption range of the crystal. The samples (rectangular shaped crystals) were cut parallel to the cleavage plane to the desired thickness of 1-2 mm and polished using silicon carbide paper. They were annealed for two hours at 150 °C to remove moisture content, if present. Opposite faces of the sample crystals were coated with good quality graphite to obtain a good ohmic contact with the electrodes. The samples were again annealed in the holder assembly at 150°C before making observations. The resistance of the crystal was measured using a megohmmeter. The observations were made while cooling the sample and temperature was controlled to an accuracy of $\pm 1^\circ\text{C}$. The dimensions of the crystal were measured using a travelling microscope. The crystal sample is well-polished and surfaces are cleaned with acetone. This is attached to a microscope slide and two electrodes of thin copper wire (0.14 cm diameter) are fixed onto the specimen at some distance apart using silver paint. After this it is annealed at a temperature of 100 °C to perfect dryness. A D.C. power supply, a Keithley 485 picoammeter and the prepared sample are connected in series. The applied field is increased from 0 to 2000 Vcm^{-1} . The sample is covered with a black cloth to avoid exposure to any radiation. The current (dark) is measured. To measure the photoconductivity, light from a 100 W halogen lamp is focused onto the sample. The current is noted for varying applied fields as before.

3. RESULTS AND DISCUSSION

3.1 Single Crystal XRD

The lattice parameters were found to be $a=14.45 \text{ \AA}$, $b=14.08 \text{ \AA}$, $c=5.85 \text{ \AA}$, $\alpha = \beta = \gamma = 90^\circ$ with unit cell volume $V = 1192.62 \text{ \AA}^3$. These lattice parameters values are found to be in good agreement with the reported values [15].

3.2. Optical Studies

UV-VIS-NIR absorption spectrophotometer was used to record the absorption spectrum in the range between 200 nm and 1000 nm. From the observed spectrum (Fig.1), the lower cut-off wavelength is found to be 400 nm. The absence of absorption in the near infrared region provides the access to the laser wavelength of 1064 nm from Nd: YAG source for second harmonic generation. Hence, UV absorption studies reveal that the grown 4-methoxy benzoin crystal is one of the suitable materials for exhibiting second harmonic generation in the entire visible and near infrared region. The measured transmittance (T) was used to calculate the absorption coefficient (α) using the relation,


$$\alpha = \frac{2.3026 \log\left(\frac{1}{T}\right)}{t} \quad (1)$$

where T is the transmittance and t is the thickness of the crystal. Optical band gap (E_g) was evaluated from the absorption spectra and optical absorption coefficient (α) near the absorption edge is given by,


$$\alpha h\nu = A(h\nu - E_g)^{1/2} \quad (2)$$

where E_g is the optical band gap of the crystal and A is a constant. The Tauc's plot of $(\alpha h\nu)^2$ against the photon energy (h ν) at room temperature (Fig.2) shows a linear behaviour, (α -absorption coefficient and h-Planck's constant) which can be considered as an evidence

86 of the indirect transition. Hence, assuming indirect transition between valence band and
 87 conduction band, the bandgap (E_g) is estimated by extrapolation of the linear portion of the
 88 curve to the point $(\alpha h\nu)^2 = 0$ [16]. Using this method, the band gap of the 4-methoxy benzoin
 89 crystal was found to be 3.50 eV. As a consequence of wide band gap, the grown crystal has
 90 large transmittance in the visible region [17].
 91

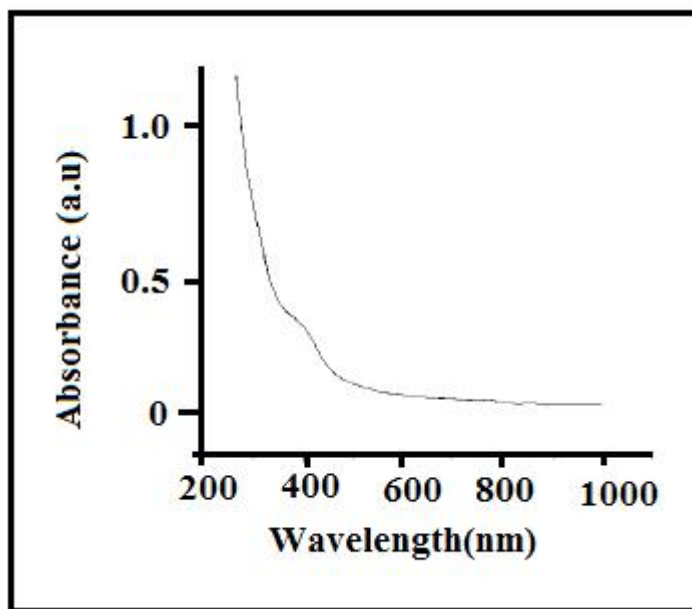

92
 93 Fig. 1. UV-VIS-NIR absorption spectrum of 4-methoxy benzoin crystal
 94
 95

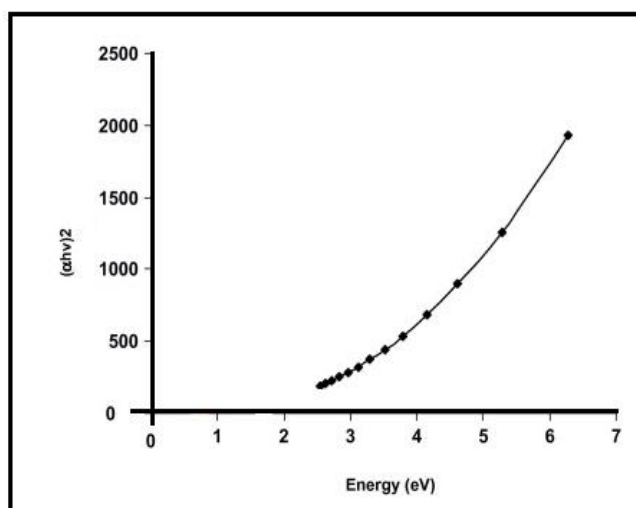

96
 97 Fig.2. Band gap of 4-methoxy benzoin crystal
 98
 99
 100
 101

102 Extinction coefficient (K) can be obtained from the following equation:

103
$$K = \frac{\lambda \alpha}{4\pi} \quad (3)$$

104 The transmittance (T) is given by

105
$$T = \frac{(1-R)^2 \exp(-\alpha t)}{1-R^2 \exp(-2\alpha t)} \quad (4)$$

106 Reflectance (R) in terms of absorption coefficient can be obtained from the above equation.

107 Hence,

108
$$R = \frac{\exp(-\alpha t) \pm \sqrt{\exp(-\alpha t)T - \exp(-3\alpha t)T + \exp(-2\alpha t)T^2}}{\exp(-\alpha t) + \exp(-2\alpha t)T} \quad (5)$$

109 Refractive index (n) can be determined from reflectance data using the following equation

110
$$n = -(R+1) \pm 2 \frac{\sqrt{R}}{(R-1)} \quad (6)$$

111 The refractive index (n) is 1.89 at $\lambda = 1000$ nm. From the optical constants, electric
112 susceptibility (χ_c) can be calculated according to the following relation [18].

113
$$\epsilon_r = \epsilon_0 + 4\pi\chi_c = n^2 - k^2 \quad (7)$$

114 Hence,

115
$$\chi_c = \frac{n^2 - k^2 - \epsilon_0}{4\pi} \quad (8)$$

116 where ϵ_0 is the dielectric constant in the absence of any contribution from free carriers. The
117 value of electric susceptibility χ_c is 0.132 at $\lambda = 1000$ nm. The real part dielectric constant
118 ϵ_r and imaginary part dielectric constant ϵ_i can be calculated from the following relations
119 [19]

120
$$\epsilon_r = n^2 - k^2 \quad \& \quad \epsilon_i = 2nk \quad (9)$$

121 The value of real ϵ_r and ϵ_i imaginary dielectric constants at $\lambda = 1000$ nm are 1.261 and
122 5.874×10^{-5} respectively.

123 3.3 DC CONDUCTIVITY STUDIES

124 There are three mechanisms of electrical conduction dielectrics (depending on the type of
125 carriers) (a) ionic or electronic conduction (b) mol ionic or electrophoretic conduction and (c)
126 electronic conduction. Dielectrics actually exhibit a combined conduction, especially ionic
127 and electronic conduction. Ionic conductivity studies provide valuable information about the
128 state of point imperfections. At any particular temperature, the Gibb's free energy of a crystal
129 is minimum when a certain fraction of ions occupy the normal lattice. As the temperature
130 rises, more and more defects are produced which, in turn, increases the conductivity. In the
131 high temperature (intrinsic) region, the effect of impurity on electrical conduction will not
132 change appreciably whereas in the low temperature (extrinsic) region the presence of
133 impurity in the crystal increases its conductivity. The electrical conduction in dielectrics is
134 mainly a defect controlled process in the low temperature region. The presence of impurities
135 and vacancies mainly determine this region. The energy needed to form the defect is much
136 larger than the energy needed for its drift. The conductivity of the crystal in the high
137 temperature region is determined by the intrinsic defects caused by thermal fluctuations in
138 the crystal. Conduction in an ionic crystal is, in general, a defect controlled property. The
139 defect concentration increases exponentially with rise of temperature and the electrical
140 conductivity increases correspondingly. Addition of divalent impurities to the crystal
141 influences the concentration of point defects. Processes like association, aggregation and
142

precipitation which become important at low temperatures and higher impurity levels, in general, reduce the free point defects that are necessary for electrical conduction. Formation, migration and association of point defects are governed by characteristic activation energies. An analytical increase in the concentration of defects both through the law of mass action and charge neutrality criterion. With the usual electric field, the charge transport by electrons in ionic crystals is zero because of a large forbidden gap. Ionic conduction occurs either through the migration of positive and negative ions in an external electric field (the ions originate either in the material in question or in interstitial impurities) or through the motion of ions in vacancies which reflects the migration of vacancies. If the sample is placed in a stationary electric field, the carriers may be considered to be contained in an enclosure bounded by the capacitor plates. As the carriers may not leave the enclosure they accumulate in the regions close to the plates which cause a concentration gradient to be formed and this gradient feeds diffusion current. At equilibrium the diffusion current density equals that of the drift current. Charge accumulation is related to the homogeneities of the material and the agglomeration of impurity ions by diffusion in the vicinity of electrodes or chemical changes in layers close to electrodes. The conductivity (σ_{dc}) of the crystal was calculated using the relation,

$$\sigma_{dc} = t / RA \quad (10)$$

where R is the measured resistance, t is the thickness of the sample and A is the area of the face in contact with the electrode. The above procedure was used to determine the DC electrical conductivity. The general relation for the temperature variation of conductivity is given by

$$\sigma_{dc} = \sigma_0 \exp[-\bar{E}/kT], \quad (11)$$

where σ_{dc} is a constant depending on material, $\bar{E}$ the activation of energy, T the absolute temperature and k the Boltzmann's constant. The above equation may be rewritten as

$$\ln \sigma_{dc} = \ln \sigma_0 [-\bar{E}/kT], \quad (12)$$

A plot of σ_{dc} versus $1000/T$ gives $-\bar{E}/k$ as the slope and $\ln \sigma_{dc}$ as the intercept. The σ_{dc} values in the temperature region studied are found to increase with temperature for 4-methoxy benzoin crystal (Fig.3 and Fig.4). Electrical conductivity depends on thermal treatment of a crystal. Thus the conductivity at low temperatures depends on the cooling speed from melting point temperature to room temperature. Thus for slow cooling, the remaking of the lattice can occur by the migration of interstitials to vacancies, recombination of Schottky defects or migration of vacancies to the surface or along dislocation channels. On quenching or rapid cooling, a fraction of the vacancies freeze and the pre-exponential term includes a contribution from those frozen vacancies. The value of conductivity $\ln \sigma_{dc}$ is found to increase with temperature. The plot of $\ln \sigma_{dc}$ versus $1000/T$ is shown in Fig.4. The activation energy calculated from the slope of the graph (Fig. 4) it is found to be 0.040 eV.

180

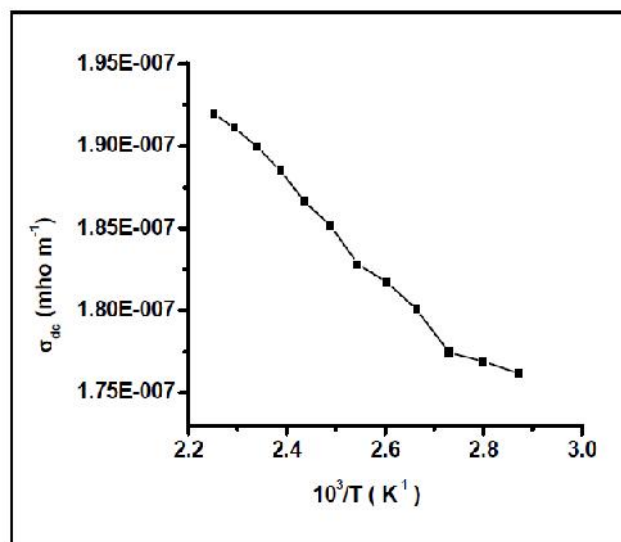


Fig.3. Variation of dc conductivity with $1000/T$ for 4-methoxy benzoin crystal

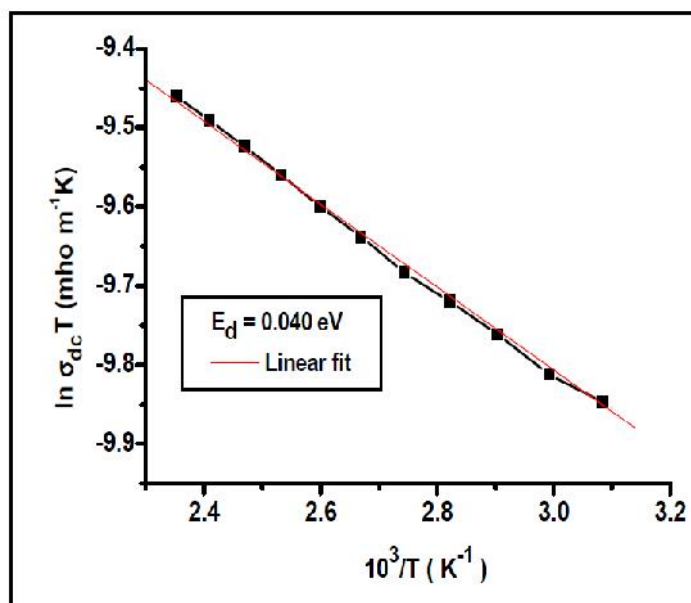


Fig.4. Plot of $\ln(\sigma_{dc})T$ versus $1000/T$ for 4-methoxy benzoin crystal

3.4 Photoconductivity Property

Photoconductivity studies have been carried out using Keithley 485 picoammeter instrument. The dark current has been recorded by keeping the crystal unexposed to any radiation. Fig.5 shows the variation of both dark current (I_d) and photocurrent (I_p) with applied electric field. It is seen from the plots that both I_d and I_p of the 4-methoxy benzoin crystal increase linearly with applied electric field. It is found from the plot that the dark current is always

higher than the photo current, thus confirming the negative photoconductivity nature of the 4-methoxy benzoin crystal. The phenomenon of negative photoconductivity is explained by Stockmann model [20]. The negative photoconductivity in a solid is due to the decrease in the number of charge carriers or their lifetime, in the presence of radiation [21]. For a negative photoconductor, forbidden gap holds two energy levels in which one is placed between the Fermi level and the conduction band while the other is located close to the valence band. The second state has higher capture cross-section for electrons and holes. As it captures electrons from the conduction band and holes from the valence band, the number of charge carriers in the conduction band gets reduced and the current decreases in the presence of radiation.

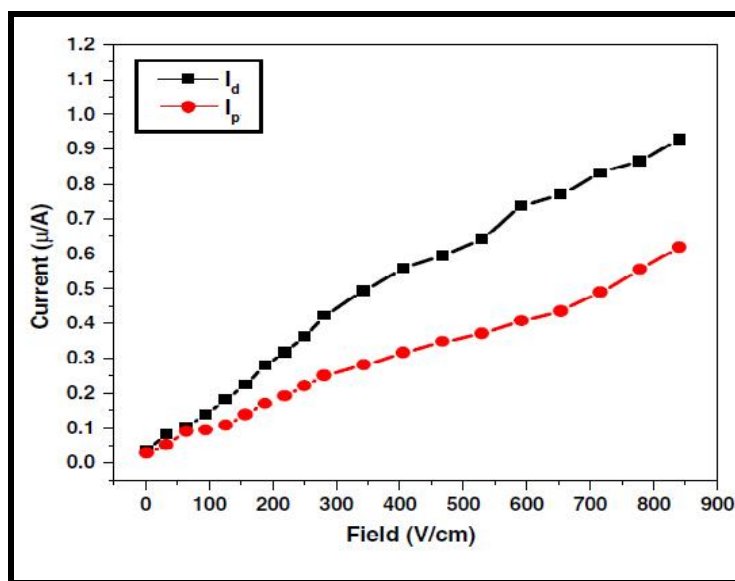


Fig.5. Field dependent photoconductivity of 4-methoxy benzoin single crystal

4. CONCLUSION

The single crystals of 4-methoxy benzoin were grown by slow evaporation technique. The lattice parameters of the grown crystals are determined by single crystal XRD. The optical absorption spectral analysis reveals that the crystal is transparent in the entire UV-VIS-NIR region with the lower cut-off wavelength as 400 nm. The optical bandgap for the grown crystal is found to be 3.50 eV. Optical band gap (E_g), absorption coefficient (α), refractive index (n), electric susceptibility χ_c and dielectric constants were calculated as a function of wavelength. The activation energy is determined from the plots of DC electrical conductivity. The photocurrent was less than the dark current, signifying negative photoconducting nature.

REFERENCES

- [1] G. Jordon, T. Kobayashi, W.J. Blau, S. Pfeiffer, H.-H. Horhold, *Advanced Functional Materials*, **2003**, 13, 751–754
- [2] Yang Z, Aravazhi S, Schneider A, Seiler P, Jazbisnek M, Gunter P, *Advanced Functional Materials*, **2005**, 15, 1072–6
- [3] Kwon O-P, Kwon S-J, Jazbisnek M, Brunner FDJ, Seo J-I, Hunziker C, *Advanced Functional Materials*, **2008**, 18, 3242–50

231 [4] Wong MS, Bosshard C, Gunter P, *Advanced Functional Materials*, **1997**, **9**,837–42
 232 [5] Kiran AJ, Kim HC, Kim K, Rotermund F, Ravindra HJ, Dharmaparakash SM, *Applied*
 233 *Physics Letters*, **2008**, 92, 113307–10
 234 [6] John Kiran A, Lee HW, Ravindra HJ, Dharmaparakash SM, Kim K, Lim H, *Current Applied*
 235 *Physics*, **2011**, 10, 1290–6
 236 [7] Bosshard C, Sutter K, Prêtre P, Hulliger J, Florsheimer M, Kaatz P, *Gordon and Breach*
 237 *Science Publishers*, **1995**
 238 [8] Zyss J. Molecular nonlinear optics: materials, physics, devices. Boston: *Academic Press*,
 239 **1994**
 240 [9] Prasad PN, Williams JD. Introduction to nonlinear optical effects in molecules and
 241 polymers. *New York, Wiley*, **1990**
 242 [10] Chemla DS, Zyss J. Nonlinear optical properties of organic molecules and crystals.
 243 Orlando, Academic Press, **1987**
 244 [11] Bosshard C, Sutter K, Schlessler R, Gunter P, *Journal of the Optical Society of America*
 245 *B*, **1993**, 10, 867–85
 246 [12] Zyss J. *Chemical Physics*, **1979**, 71, 909–16
 247 [13] Levine BF, Bethea CG, Thurmond CD, Lynch RT, Bernstein JL, *Journal of Applied*
 248 *Physics*, **1979**, 50, 2523–7
 249 [14] Prasad PN, Williams DJ. Introduction to nonlinear optical effects in organic molecules
 250 and polymers. *New York, Wiley*, **1991**
 251 [15] G. Thanujav, G. Nithya and C. Kanagam, *Photonics letters of Poland*, **2012**, 4 (1), 41–43
 252 [16] Eya DDO, Ekpunobi AJ, and Okeke CE, *Acad. Open Internet J.* **2006**; **17**
 253 [17] K. Sangwal, *Mater. Chem. Phys.*, **2000**, 63, 145.
 254 [18] Gupta V, Mansingh A. *J. Appl. Phys.*, **1996**, 80, 1063.
 255 [19] Gaffar MA, Abu El-Fadl A, Bin Anooz S. *Physica B*, **2003**, 327, 43.
 256 [20] Joshi V N, *Photoconductivity*, Marcel Dekker, New York, **1990**.
 257 [21] R. H. Bube, *Photoconductivity of solids*, Wiley, New York, **1981**
 258
 259
 260
 261
 262
 263
 264
 265
 266
 267
 268
 269
 270
 271