

Grinding-assisted Solid-State Metathetic Synthesis of Divalent Transition Metal Tungstates

U. Sujana Kumari^{1*}, P. Suresh², A. V. Prasada Rao³

^{1, 2, 3} Department of Inorganic and Analytical Chemistry, Andhra University, Visakhapatnam, 530003, India.

ABSTRACT

A convenient solid state metathetic synthesis has been developed for the preparation of metal tungstates MWO_4 where $M = Mn, Fe, Co, Ni$ and Zn using Na_2WO_4 and respective MCl_2 as reactants. Stoichiometric quantities of respective reactants were mixed and ground for 2hrs. XRD patterns of the homogenised mixture heat treated at $400^\circ C$ for 4hrs and then washed free from $NaCl$ by product were in good agreement with the respective JCPDS data showing the formation of phase pure compounds in each case without any contamination. Microstructural investigation indicated particle size of the order of μm .

Keywords: Solid state metathesis, Manganese tungstate, Iron tungstate, Cobalt tungstate, Nickel tungstate, Zinc tungstate.

1. INTRODUCTION

MWO_4 type compounds where M is a divalent transition metal ion have attracted a lot of scientific interest in recent times because of their many useful properties. These compounds exist in two different crystal structures namely Scheelite and wolframite. Bivalent metal ions with large ionic radius such as Ca^{2+} , Sr^{2+} , Ba^{2+} and Pb^{2+} prefer to form scheelite type structures whereas metal ions with smaller ionic radius viz. Zn^{2+} , Fe^{2+} , Co^{2+} , Ni^{2+} and Cd^{2+} tend to crystallize in wolframite type of structure. Crystal structure of Scheelite $CaWO_4$ is tetragonal with calcium surrounded by eight oxygens with isolated tetrahedra of WO_4 being nearly regular, whereas in wolframite each W is coordinated to six oxygens unlike scheelite. MWO_4 type divalent transition metal compounds have been reported to be useful for humidity sensors [1], photocatalysts [2], photochromic [3] and as photoanodes [4].

3d transition metal tungstate powders have been synthesized by different techniques such as solid-state reaction [5], chemical synthesis [6-10], hydrothermal [11-13], microwave hydrothermal [14], self propagation [15], template synthesis [16], combustion [17], molten salt [18] and aqueous salt metathetic reaction [19]. Among these methods, solid-state

* Tel.: +91-9490149128.

E-mail address: sujana.uriti1@gmail.com.


reactions invariably involve higher temperatures of more than 800⁰C while solution based chemical methods require special equipment and subsequent annealing of amorphous or nano powders to temperatures above 500⁰C for several hours to render them into crystalline form. Compared to these two basic approaches, solid-state metathesis (SSM) offers a easy and convenient route for the synthesis of many mixed metal oxides. These reactions involve double exchange with preferred formation of an alkali halide with large lattice energy which favours the reactions at lower temperatures compared to solid-state reactions between constituent metal oxides. SSM has been successfully employed for the synthesis of perovskite oxides [20], ordered double perovskites [21], LaAlO₃ [22], Bi₂WO₆ [23] and molybdates [24].

In continuation of our earlier work relating to room temperature solid-state metathetic synthesis of Ca, Sr, Ba, Pb and Cd tungstates and synthesis of phase pure BaSnO₃ and BaZrO₃ we now report the solid-state metathetic synthesis of transition metal tungstates MWO₄ where M²⁺ = Fe, Mn, Co, Ni and Zn. Since the transition metal tungstates are potential photocatalysts in the visible region [6] for the degradation of organic pollutants from the industrial exhausts, synthesis of these compounds at lower temperatures so as not to effect the surface area of support is highly essential.

2. EXPERIMENTAL

2.1 Sample Preparation

Metal chlorides, MCl₂ (where M=Fe, Mn, Co, Ni and Zn) along with Na₂WO₄ are used as precursors. All the starting materials were analytical grade and were utilized as received without further purification. Stoichiometric quantities of the reactants were weighed and the mixture was ground in an agate mortar for 2hrs with addition of ethanol as per the reaction given below.



The homogenised mixture was dried in an air oven and subjected to heat treatment at different temperatures. The resultant solid was washed with water until free from chloride and the residue after drying was characterised for phase identification by X-ray diffraction(XRD).

2.2. Characterization Techniques

Phase purity of the final calcined powders was investigated with x-ray diffractometer (PANalytical- X' Pert PRO, Japan) at room temperature, using Nickel filter Cu-K_α radiation (λ= 1.54059 Å), over a wide range of 10° ≤ 2θ ≤ 80° with a scanning speed of 2° min⁻¹. Microstructural investigations of the samples were performed on the fractured surface of the sample using SEM (JEOL-JSM-6610LV, Tokyo, Japan). Energy Dispersive X-ray Spectroscopy (EDS) was used to detect x-rays emitted from the sample during bombardment with an electron beam to identify the elemental composition of the analyzed volume. Raman spectra were recorded using SENTERRA from BRUKER Corporation.

3. RESULTS AND DISCUSSION

XRD patterns obtained for homogenised mixtures of $MCl_2 + Na_2WO_4$ (where $M = Fe, Mn, Co, Ni$ and Zn) subjected to heat treatment at $400^\circ C$ for 4hrs followed by washing with water until free from chloride and dried are given in Figures 1 to 4. XRD patterns of homogenised mixture of $NiCl_2 + Na_2WO_4$ at room temperature and heat treated at $300^\circ C$ and $400^\circ C$ for 4hrs followed by washing are shown in Fig.1. XRD patterns indicate formation of well crystalline $NiWO_4$ only for the sample heat treated at $400^\circ C$ for 4hrs. All the peaks in the XRD pattern could be indexed as the observed pattern is in good agreement with that of $NiWO_4$ given in JCPDS file no.15-0755. No extra peaks were noticed which indicates the formation of phase pure sample. Observed XRD patterns below $400^\circ C$ does not match with the highest intensity peaks of $NiCl_2$, Na_2WO_4 and $NaCl$. Hence these peaks may be ascribed to amorphous precursor with some partially crystalline $NiWO_4$.((002), (022) and (220) peaks).

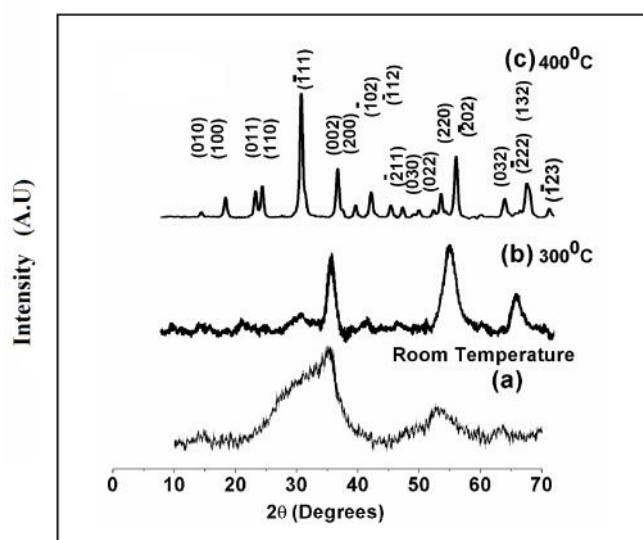


Fig. 1. XRD patterns of stoichiometric mixture of $NiCl_2 + Na_2WO_4$ ground for 2hrs a) room temperature b) heat treated at $300^\circ C$ for 4hrs c) heat treated at $400^\circ C$ for 4hrs and washed free of chloride.

Fig 2 shows the XRD patterns of homogenised mixture of stoichiometric amounts of $ZnCl_2$ and Na_2WO_4 , ground for 2 hrs at room temperature and subjected to heat treatment of $400^\circ C$ for 4hrs, both washed free of chloride and dried. The washed product of $ZnWO_4$ at room temperature did not indicate any sharp peaks characteristic of the reactants or $NaCl$ by product. The broad peak coincides with the 100% intensity peak of $ZnWO_4$ and this can be attributed to $ZnWO_4$ in the amorphous form. However, when subjected to heat treatment at $400^\circ C$, characteristic peaks due to formation of well crystalline phase pure $ZnWO_4$ were obtained and the data is in agreement with that reported in JCPDS file no.73-0554.

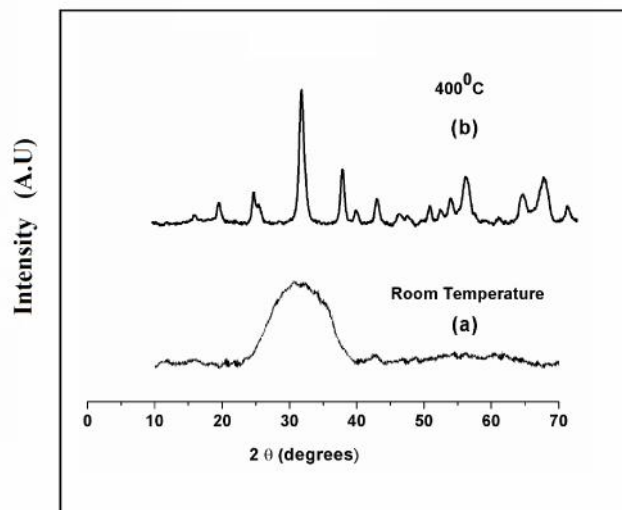


Fig. 2. XRD patterns of stiochiometric mixture of $\text{ZnCl}_2 + \text{Na}_2\text{WO}_4$ ground for 2hrs a) room temperature, b) heat treated at 400°C for 4hrs

Fig 3 shows the XRD patterns obtained for mixtures of $\text{MnCl}_2 + \text{Na}_2\text{WO}_4$ and $\text{CoCl}_2 + \text{Na}_2\text{WO}_4$ ground for 2hrs and heated at 400°C for 4hrs followed by washing to remove NaCl. The observed XRD patterns are in good agreement with the reported data for MnWO_4 and CoWO_4 of JCPDS files 80-0134 and 72-0479 respectively. Miroslaw Maczka et al [25] reported two different synthesis routes for MnWO_4 (i) a hydrothermal method using ethanolamine and CTAB and (ii) by annealing a precursor obtained by co-precipitation. In their second method, XRD patterns were indicative of nanocrystalline MnWO_4 formation with crystallite size smaller than 20 and 26 nm when the synthesis was performed at 250 and 400°C , respectively. In the present method sharp peaks characteristic for large and well-crystallized MnWO_4 particles were revealed for annealing at 400°C for 4 hrs.

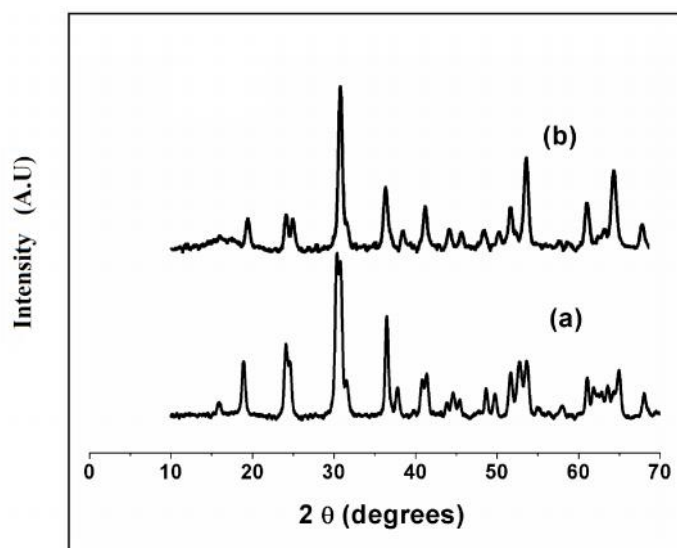


Fig. 3. XRD patterns of stoichiometric mixture of a) $\text{MnCl}_2 + \text{Na}_2\text{WO}_4$ ground for 2hrs and heat treated at 400°C for 4hrs, washed and dried. b) $\text{CoCl}_2 + \text{Na}_2\text{WO}_4$ ground for 2hrs, heat treated at 400°C at 4hrs, washed and dried.

Fig 4 shows the XRD patterns obtained for mixture of $\text{FeCl}_2 + \text{Na}_2\text{WO}_4$ ground for 2hrs and heat treated at 400°C for 2hrs and at 600°C for 3hrs and washed free from NaCl by product. Though the formation of FeWO_4 is evident at 400°C , for unambiguous indexing of peak positions, the sample is subjected to heat treatment at 600°C for 3hrs to render it more crystalline. All peaks for the resultant sample could be indexed in accordance with JCPDS file no. 71-2391.

Synthesis of MWO_4 powders was reported by solution based metathesis reaction using equimolar solutions of metal nitrates and sodium tungstate, with subsequent heating of the precipitate to 800°C for 15hr [19]. Parhi et al [26] reported synthesis of ZnWO_4 , NiWO_4 and MnWO_4 by microwave assisted solid-state metathesis using 2.45 GHz microwave frequency and a power of 1100 W for 10 minutes duration. Though crystalline ZnWO_4 was obtained at room temperature by this process, crystalline MnWO_4 and NiWO_4 were obtained only after heat treatment at 500°C for 6hrs. Angana sen et al [8] reported the synthesis of Co, Ni, Cu and Zn metal tungstates from the complete evaporation of polymer based metal-complex precursor solution subjected to heat treatment. Rajagopal [27] reported the hydrothermal synthesis of FeWO_4 and CoWO_4 using sodium tungstate with ferrous ammonium sulphate and cobalt chloride solutions as precursors respectively. Recently Garcia-Perez et al [7] reported the synthesis of Co, Cu, Mn and Ni tungstates by co-precipitation method at 400°C . Tiziano Montini et al reported the synthesis of transition metal tungstates $\text{M}^{\text{II}}\text{WO}_4$ ($\text{M} = \text{Co}^{\text{II}}$, Ni^{II} , Cu^{II} , Zn^{II}) by reaction of transition metal nitrates with sodium tungstates and then subjected to heat treatment at 500°C . The SSM synthesis reported in the present study is the lowest synthesis temperature reported for solid-state synthesis. It is less cumbersome and could be performed at ambient pressure.

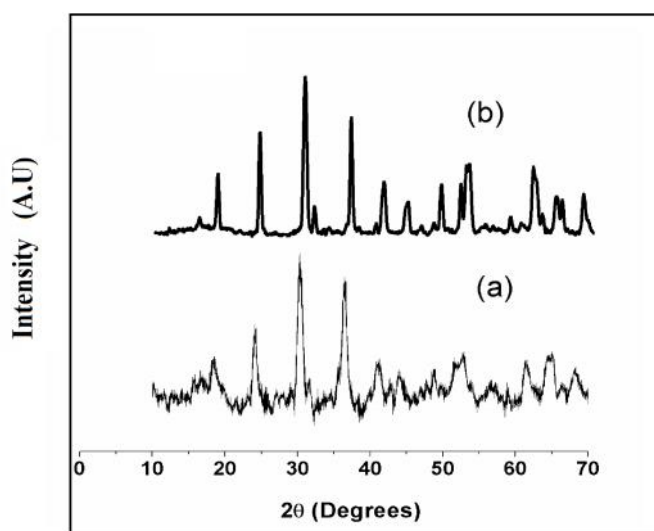


Fig. 4. XRD patterns of stoichiometric mixture of $\text{FeCl}_2 + \text{Na}_2\text{WO}_4$ ground for 2hrs and heat treated at a) 400°C for 4hrs b) 600°C for 3hrs and washed free of chloride.

Fig 5 shows Raman spectra of MnWO_4 , FeWO_4 , CoWO_4 , NiWO_4 and ZnWO_4 In terms of group theoretical analysis, wolframite structure belonging to $\text{P2}/c$ ($z = 2$) monoclinic structure

is expected to give 18 ($8A_g + 10 B_g$) Raman-active bands out of 36 possible lattice modes[28]. Raman spectra for all samples revealed peaks due to $8A_g$ (breathing of tungstate tetrahedra) vibrations while some peaks due to $10B_g$ were not resolved. Based on the previos reports, the most intense band in $ZnWO_4$ was ascribed to antisymmetric bridging mode associated with the tungsten chain [13]. In MnO_4 the band at 127 cm^{-1} accompanied by two weak bands in the range 160 and 180 cm^{-1} were ascribed to interchain deformation and torsion modes [14]. Though extensive studies on Raman spectra of some of these tungstates were reported in the literature subsequently [29], we at this stage did not make an elaborate interpretation of Raman spectra as our interest is limited to show the phase formation of tungstates only. Our data is in agreement with those reported earlier [13],[14],[28].

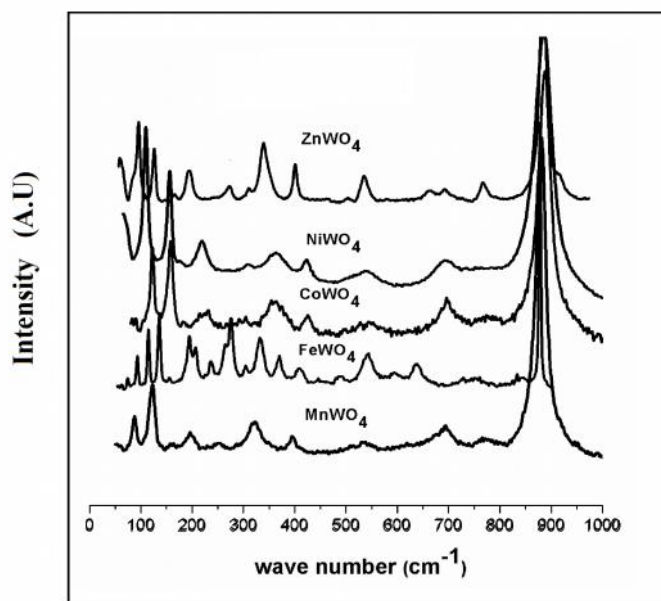


Fig. 5. Raman spectra of $MnWO_4$, $CoWO_4$, $NiWO_4$ and $ZnWO_4$ heat treated at 400°C and $FeWO_4$ heat treated at 600°C .

SEM micrograph of a representative sample $FeWO_4$ powder heat treated at 600°C is shown in fig. 6 which shows particles of different sizes due to aggregation. Elemental analysis of the sample confirms the presence of Fe, W and O, with no extra lines due to any contamination.

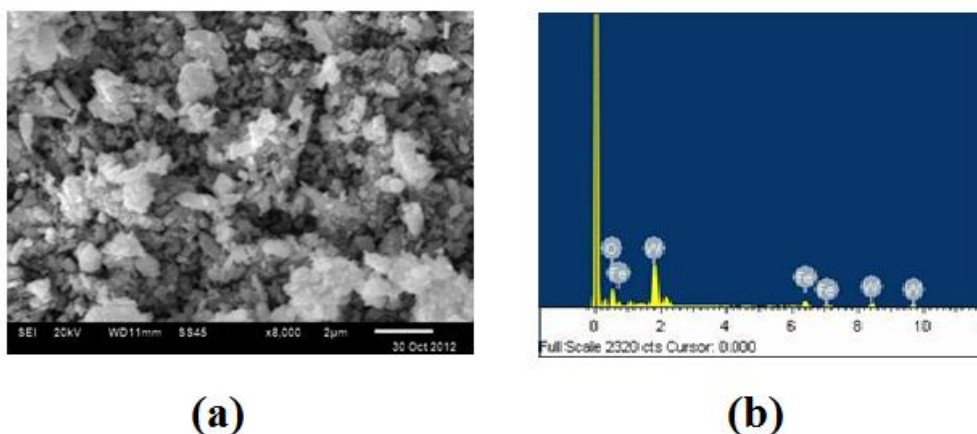


Fig. 6. a) SEM image of FeWO₄ powder and b) EDS of the FeWO₄ powder under SEM investigation.

4. CONCLUSION

A simple low temperature solid state metathetic synthesis is reported for the preparation of MWO₄ (M = Fe, Mn, Co, Ni and Zn) powders using respective metal chlorides and sodium tungstate as precursors. XRD patterns of respective powders obtained by mixing stoichiometric quantities of the reactants, ground for two hours followed by heat treatment at 400°C for 4hrs, and washed free of chloride indicated formation of respective phase pure metal tungstates. Reaction temperatures reported for the synthesis of transition metal tungstates are less compared to these solid-state method. The process is costeffective and simple. Microstructural investigation indicated particle aggregation.

ACKNOWLEDGEMENTS

One of the authors (sujana kumari) gratefully acknowledges the research supervisor prof. A.V.Prasada Rao for the constant encouragement throughout research work.

REFERENCES

1. Bhattacharya AK, Biswas RG, Hartridge A. Environment sensitive impedance spectroscopy and DC conductivity measurements on NiWO₄. J. Mater. Sci. 1997;32(2):353-356.
2. Huang G, Zhu Y. Synthesis and photocatalytic performance of ZnWO₄ catalyst. Mater Sci. Eng.B. 2007;139(2/3):201-208.
3. Kuzmin A, Purans J, Kalendarev R, Pailharey D, Mathey Y. XAS, XRD, AFM, and Raman studies of nickel tungstate electrochromic thin films. Electrochim. Acta 2001;46:2233-2236.
4. Pandey PK, Bhawe NS, Kharat RB. Structural, Optical, electrical and photovoltaic electrochemical characterization of spray deposited NiWO₄ thin films. Electrochim. Acta. 2006;51(22):4659-4664.
5. Bhaskar Kumar G, Sivaiah K, Buddhudu S. Synthesis and characterization of ZnWO₄ ceramic powder. Ceram. Inter. 2010; 36:199-202.

- 225 6. Tiziano Montini, Valentina Gombac, Abdul Hameed, Laura Felisari, Gianpiero
226 Adami, Paolo Fornasiero. Synthesis, Characterization and photocatalytic performance
227 of transition metal tungstates. *Chem. Phys. Lett.* 2010;498:113-119.
- 228 7. Garcia Perez UM, Martinez-de la Cruz A, Peral J. Transition metal tungstates
229 synthesized by co-precipitation method: Basic photocatalytic properties. *Electrochim.*
230 *Acta*, 2012; 81:227-232.
- 231 8. Angana Sen, Panchanan Pramanik. A chemical synthetic route for the preparation
232 of fine-grained metal tungstate powder (M= Ca, Co, Ni, Cu, Zn). *J. Eur. Ceram. Soc.*
233 2001;21:745-750.
- 234 9. Kalinko A, Kuzmin A. Raman and Photoluminescence spectroscopy of
235 Zingtungstate powders. *J. Lumin.* 2009;129:1144-1147.
- 236 10. Aleksandr Kalinko, Alexey Kotlov, Alexei Kuzmin, Vladimir Pankratov, Anatoli I.
237 Popov, Liana Shirmana. Electronic excitations in ZnWO_4 and $\text{Zn}_x\text{Ni}_{1-x}\text{WO}_4$ ($x=0.1-0.9$)
238 using VUV synchrotron radiation. *Cent. Eur. J. Phys.* 2011; 9(2):432-437.
- 239 11. Fu-Shan Wen, Xu Zhao, Hua Huo, Jie-Sheng Chen, E. Shu-Lin, Jia- Hua Zhang.
240 Hydrothermal Synthesis and photoluminescent properties of ZnWO_4 and Eu^{3+} -doped
241 ZnWO_4 . *Mater. Lett.* 2002;55:152-157.
- 242 12. Qiang Wang, Mingming Sun, Chunhong Li. Hydrothermal synthesis and
243 photoluminescent properties of zinc tungstate Nano/Micro structures. *Adv. Mater. Res.*
244 2011;328-330:1580-1584.
- 245 13. Hongbo Fu, Chengsi Pan, Liwu Zhang, Yongfa Zhu. Synthesis, Characterization
246 and photocatalytic properties of nanosized Bi_2WO_6 , PbWO_4 and ZnWO_4 catalysts.
247 *Mater. Res. Bull.* 2007;42:696-706.
- 248 14. Theo Klopogge J, Matt L. Weier, Loc V. Duong, Roy L. Frost. Microwave-assisted
249 synthesis and characterisation of divalent metal tungstates nano crystalline minerals:
250 ferberite, hubnerite, sanmartinite, scheelite and stolzite. *Mater. Chem. and Phys.*
251 2004;88:438-443.
- 252 15. Tiaotiao Dong, Zhaohui Li, Zhengxin Ding, Ling Wu, Xuxu Wang, Xianzhi Fu.
253 Characterizations and properties of Eu^{3+} -doped ZnWO_4 prepared via a facile self-
254 propagating combustion method. *Mater. Res. Bull.* 2008;43:1694-1701.
- 255 16. Hongjun Zhou, Yuen Yiu, Aronson MC, Stanislaus S. Wong. Ambient template
256 synthesis of multiferroic MnWO_4 nanowires and nanowires arrays. *J. Solid State Chem.*
257 2008;181:1539-1545.
- 258 17. Larisa Gigorjeva, Donats Millers, Janis Grabis, Dzidra Jankovica.
259 Photoluminescence and photocatalytic activity of zinc tungstate powders. *Cent. Eur. J.*
260 *Phys.* 2011;9 (2):510-514.
- 261 18. Yakubovskaya AG, Katrunov KA, Tupitsyna IA, Starzhinskiy NG, Nagornaya LL,
262 Zhukov AV, Zenya IM, Baumer VN, Vovk OM. Nanocrystalline Zinc and cadmium
263 tungstates: morphology, luminescent and scintillation properties. *Funct. Mater.* 2011;18
264 (4):446-451.
- 265 19. Sagrario M. Montemayor, Antonio F. Fuentes. Electrochemical characteristics of
266 lithium insertion in several 3D metal tungstates (MWO_4 , M= Mn, Co, Ni and Cu)
267 prepared by aqueous reaction. *Ceram. Int.* 2004;30:393-400.
- 268 20. Radha Velchuri, Vijaya kumar B, Rama Devi V, Prasad G, Vithal M. Solid State
269 Metathesis of BaTiO_3 , PbTiO_3 , $\text{K}_{0.5}\text{Bi}_{0.5}\text{TiO}_3$ and $\text{Na}_{0.5}\text{Bi}_{0.5}\text{TiO}_3$. *Ceram. Int.* 2010;36:
270 1485-1489.
- 271 21. Siva Kumar T, Lofland SE, Ramanujachary KV, Ramesha K, Subbanna GN,
272 Gopalakrishnan J. Transforming $n=1$ members of the Ruddlesden-Popper phases to a
273 $n=3$ member through metathesis: synthesis of a layered perovskite, $\text{Ca}_2\text{La}_2\text{CuTi}_2\text{O}_{10}$. *J.*
274 *Solid State Chem.* 2004;177:2635-2638.
- 275 22. Mirosław Maczka, Esmeralda Mendoza-Mendoza, Antonio F Fuentes, Karol
276 Lemanski, Przemysław Deren. Low-temperature synthesis, luminescence and phonon

277 properties of Er and/or Dy doped LaAlO_3 nanopowders. J. Solid State Chem.
 278 2012;187:249-257.
 279 23. Maczka M, Fuentes AF, Kepinski L, Diaz-Guillen MR, Hanuza J. Synthesis and
 280 electrical, optical and phonon properties of nanosized Aurivillius phase Bi_2WO_6 . Mater.
 281 Chem. and Phys. 2010;120:289-295.
 282 24. Thangadurai V, Knittlmayer C, Weppner W. Metathetic room temperature
 283 preparation and characterization of scheelite-type ABO_4 (A=Ca, Sr, Ba, Pb; B=Mo, W)
 284 powders. Mater. Sci. and Eng. B 2004;106:228-233.
 285 25. Mirosław Maczka, Maciej Ptak, Michalina Kurnatowska, Leszek Kepinski, Paweł
 286 Tomaszewski, Jerzy Hanuza. Phonon properties of nanosized MnWO_4 with different
 287 size and morphology. J. Solid State Chem. 2011;184:2446-2457.
 288 26. Purnendu Parhi, Karthik TN, Manivannan V. Synthesis and characterization of
 289 metal tungstates by novel solid-state metathetic approach. J. Alloys and Compd.
 290 2008;465:380-386.
 291 27. Rajagopal S, Nataraj D, Khyzhun O Yu, Yahia Djaoued, Robichaud J, Mangalaraj
 292 D. Hydrothermal synthesis and electronic properties of FeWO_4 and CoWO_4
 293 nanostructures. J. Alloys and Compd. 2010;493 (1-2): 340-345.
 294 28. Kislá P. F. Siqueira, Anderson Dias. Incipient crystallization of transition-metal
 295 tungstates under microwaves probed by Raman scattering and transmission electron
 296 microscopy. J. Nanopart. Res. 2011;13:5927-5933.
 297 29. Maczka M, Ptak M, Hermanowicz K, Majchrowski A, Pikul A, Hanuza J. Lattice
 298 dynamics and temperature-dependent Raman and Infrared studies of multiferroic
 299 $\text{Mn}_{0.85}\text{Co}_{0.15}\text{WO}_4$ and $\text{Mn}_{0.97}\text{Fe}_{0.03}\text{WO}_4$ crystals. Phys.Rev.B. 2011;83:174439..
 300
 301
 302