

Electronic Transport at Low temperature in Ni/Al/Ni Films

ABSTRACT

A series of sandwiched films in the configuration, Ni(100nm)/Al(t)/Ni(100nm); t = 10nm, 20nm,....., 100nm (labeled as NAN1, NAN2, ..., NAN10) were produced by thermal and electron beam gun evaporation techniques. The films were deposited onto the glass substrates held at 200 °C, under high vacuum conditions in a Hindhivac coating unit. The structure, grain size and interplanar distances were probed by X-ray diffraction (XRD). The grain sizes obtained were in the order of few nanometers and decreased with increasing, t. Electrical resistivity in the temperature range from 4K to 300K has been measured in an Oxford Instruments make resistivity measurement setup. The resistivity decreased nonlinearly and continuously with increasing temperature for the films NAN1, NAN3 and NAN7 similar to that of a semiconductor. Mott's small polaron hopping and variable range hopping models due to Mott and Greave have been employed to understand resistivity variation with temperature. In the remaining films resistivity decreased up to some temperature and increased thereafter. This indicated a kind of transition occurring in these films from metallic to semiconductor (MST). These results are significant as neither of the constituent layers in the present films is semiconducting by nature. The resistivity variation with temperature of some of these films has been analyzed using semi-classical conductivity model of Boltzman which incorporates quantum corrections in to it. It is for the first time that the sandwiched films of the present configuration have been investigated for structure and low temperature resistivity and data analyzed thoroughly.

Keywords: [Sandwich films, XRD, metal to semiconductor transition, resistivity]

1. INTRODUCTION

Currently there is enormous interest in layered magnetic films that may be due to the fact that layering can be used for tuning the properties or to obtain properties which were not characteristic of their bulk forms. For practical reasons, the present work is restricted to the study of a simple structure consisting of two magnetic layers separated by a layer of nonmagnetic material. Very extensive experimental and theoretical investigations on exchange coupling [1-3] and magneto-optical kerr-effect [4, 5] have been reported on some of these kinds of structures. In some studies, chromium (Cr) spacer instead of copper like metal has been used and investigated the effects of interface roughness [6, 7], magnetic and electronic structures [8]. An anomalous behavior of low temperature resistivity has been observed in the structure, Co/M/Co (M = Cr or Cr/Ag or Ag/Cr) [9]. The effect of Cu interlayer on grain size and stress has been investigated in sputtered Fe/Cu multilayers [10]. The structural properties were studied for Fe/Cu multilayers as a function of Fe layer thickness [11]. Some of these studies were aimed at optimizing the planar structure of (111) Au/Co/Cu trilayers [12]. The detailed studies of structure, surface morphology and low temperature electrical properties of Ni/Al/Ni

sandwiches have not been reported so far. Hydrogen doping in ZnO has the potential to reveal interesting electrical and optical properties because of its tendency to form easy bonding with charged ions [13]. Pure semiconducting behavior has been observed in oxidized Ni films [14] and a sign for metal to semiconductor transition has been noticed in Pb film [15] at low temperature. Metallic behavior of electrical conductivity at low temperature has been detected in Fe/Cu/Fe sandwiched films [16]. In the present article, we report investigations on structural and electrical properties of Ni/Al/Ni films for different Al spacer layer thicknesses. The layer structure of these films are, [Ni(100nm)/Al(t)/Ni(100 nm)]; t = 10 nm, 20 nm, 30 nm, 40 nm, 50 nm, 60 nm, 70 nm, 80nm, 90nm and 100 nm.

2. MATERIAL AND METHODS / EXPERIMENTAL DETAILS / METHODOLOGY (ARIAL, BOLD, 11 FONT, LEFT ALIGNED, CAPS)

The sandwich films, (Ni/Al/Ni) were prepared using electron beam gun and thermal evaporation techniques at a pressure 7×10^{-6} mbar and temperature 200 °C. The films were deposited onto the well cleaned glass substrates held at a temperature of 473 K. The nickel layers were deposited by evaporating the nickel source from a molybdenum crucible using electron beam gun technique, where as aluminum layers were deposited by thermally evaporating the source from a tungsten filament. The thickness of the layers was measured during deposition using quartz crystal thickness monitor. The films were annealed to room temperature in the vacuum chamber and were subjected to XRD studies in Brucker-D8 advance diffractometer with Cu-K α radiation of 1.5406 Å wavelength. Electrical resistivity was measured by following four point method in an Oxford Instruments make resistivity setup in the temperature range from 5 K to 300 K.

3. RESULTS AND DISCUSSION

3.1. X-ray diffraction (XRD) studies

The complete XRD spectrum for NAN1 film and Gaussian fit for the peak are shown in Figs. 1(a) and 1(b) respectively. Similar spectra were recorded for all the films. The spectra consist of single peak that could be due to the intermixing of the constituent layers i.e., Ni and Al. This is evident from the peak positions of different films which lie between $2\theta = 44.29^\circ$ and 44.61° [Table.1]. These peak positions do not correspond to either fcc Ni(111) or fcc Al(200). Peak position shifted slightly towards higher angle as the interfacial layer thickness increased. The average grain sizes were estimated using Scherrer's formula [17], $D = (0.9\lambda)/(B \cos\theta_B)$, where D defines the grain size, B the angular width in terms of 2θ , θ_B the Bragg angle and λ the wavelength of the radiation. The interplanar spacing of the films were calculated using the relation, $d = \lambda/(2 \sin \theta_B)$.

The structure of the spectra around the peak for all the films have been analyzed and the grain sizes and interplanar spacing were determined (Table 1). These grain sizes obtained are of only few nanometers indicating that the present films are nanocrystalline in nature. The interplanar spacing is lying between 2.029 Å and 2.043 Å. The measured peak widths are in the range of 0.638 Å and 0.945 Å. This reveals that the microstructure of the films slightly differs from film to film.

Table 1: Parameters extracted from XRD spectra for NAN sandwiched films.

Film	Thickness of Al, t (nm)	Peak position, 2θ (Å)	Peak width Å	Grain size, D (nm)	Interplanar spacing, d (Å)
NAN1	10	44.359	0.754	11.37	2.040
NAN2	20	44.346	0.945	9.077	2.041
NAN3	30	44.294	0.685	12.51	2.043
NAN4	40	44.374	0.756	11.35	2.040
NAN5	50	44.392	0.694	12.37	2.039
NAN6	60	44.516	0.698	12.29	2.033
NAN7	70	44.491	0.690	12.44	2.034
NAN8	80	44.524	0.798	10.76	2.033
NAN9	90	44.573	0.662	12.96	2.031
NAN10	100	44.610	0.638	13.47	2.029

3.2 Electrical Conductivity

The measured temperature variation of resistivity of all the present films revealed the following information.

- The films NAN1, NAN3 and NAN7 behaved like semiconductors.
- Remaining all the seven films exhibited metal to semiconductor transition (MST).

The MST transition temperatures, T_c , are shown in Table.2. Typical plots of temperature variation of ρ for NAN1, NAN4 and NAN10 films are depicted in Fig.2. From the figure, it can be seen that in the entire experimental range of temperature NAN1 film behave like a semiconductor. That is, its resistivity decreases continuously with increasing temperature. NAN3 and NAN7 films behaved exactly in the same fashion. NAN4 film exhibited metal to semiconductor transition measuring minimum resistivity at transition temperature, T_c . Transition temperature did not vary systematically with interlayer thickness as can be seen in Table.2. NAN5 film produced exactly the same type of ρ vs T spectrum. Whereas NAN10 film along with NAN2, NAN6, NAN8 and NAN9 measured a short tail on the semiconducting side although MST is quite evident in these film also.

Table.2: The MST transition temperatures, T_c , of NAN sandwich films

Films →	NAN2	NAN4	NAN5	NAN6	NAN8	NAN9	NAN10
T_c (K) →	41.12	88.24	80.69	13.96	36.53	24.36	21.43

3.2.1. Resistivity variation of NAN1, NAN3 and NAN7 films

Resistivity of NAN1, NAN3 and NAN7 films are in the order of $10^{-6} \Omega m$. The room temperature conductivity of these films are in agreement with Nio thin film [18] and higher than that of thick Nio films and Nio nano crystals [19,20]. Resistivity of these three films decreased continuously with increase in temperature resembling semiconductor behavior. The conductivity data of these films has been analysed using Mott's small polaron hopping and variable range hopping models due to Mott's and Greaves. For higher temperature, Mott's SPH model gave an expression for conductivity as

$$\sigma = (\sigma_0 / T) \exp(-\Delta E / k_B T) \quad (1)$$

Where ΔE is the activation energy and σ_0 the pre-exponential factor [21]. The plots of $\ln(\sigma T)$ versus $(1/T)$ for these three films are shown in Fig.3. The least square linear lines were fit to the data for temperatures above θ_D , where θ_D is the Debye's temperature below which the data deviates from linearity. From the slopes, the activation energy, ΔE , was determined and tabulated in Table.3. These activation energy values are smaller than that reported for NiO films and nanocrystals [18-20].

For the data below θ_D , the variable-range hopping (VRH) models due to Mott [22] and Greave [23] have been applied. In Mott's VRH model, the conduction is based on a single optical phonon approach and the conductivity is expressed as,

$$\sigma = A \exp(-T_0/T)^{1/4} \quad (2)$$

Where, $T_0 = 256 [2\alpha^3/9\pi K_B N(E_F)]$ and $A = [e^2/2(8\pi)^{1/2}] v_0 [N(E_F)/\alpha K_B T]^{1/2}$

Where $N(E_F)$ is the density of states at the Fermi level. The constants A and T_0 are obtained from the $\ln(\sigma)$ versus $T^{-1/4}$ plots as shown in Fig.4. Only part of the data below θ_D for which the Mott's VRH model fit was in good agreement, is only shown in Fig.4. It is commonly held that much use of the exponent T_0 has been made to extract values of $N(E_F)$, given assuming value for $\alpha = 10 \text{ nm}^{-1}$ [24,25]. The $N(E_F)$ values obtained are shown in Table 3. These $N(E_F)$ values are much higher than that quoted for NiO nanocrystals [20].

The data deviated from Mott's VRH has been considered under Greaves VRH model [23]. According to this model the conductivity is given by

$$\sigma T^{1/2} = B \exp(-T_0/T)^{1/4} \quad (3)$$

Where, $T_0 = (2.1)^4 [\alpha^3 / k_B N(E_F)]$

The Greaves plots of $\ln(\sigma T^{1/2})$ versus $T^{-1/4}$ are shown in Fig.5. From the fit parameters of B and T_0 , the density of states $N(E_F)$ due to Greaves model were estimated and tabulated in Table.3. Both the VRH models appear to fit well with the data in certain range of temperature. However, $N(E_F)$ values derived from them are high compared to that of the reported values for other thin films [23]. It can therefore be concluded that the conductivity of the present films at very low temperatures cannot be satisfactorily explained using Mott's and Greaves VRH models.

Table.3: Activation energy, ΔE and density of states, $N(E_F)$ determined from Mott's and Greaves model fits.

Film	Mott's SPH (meV)	ΔE	Mott's VRH	Greaves VRH
			$N(E_F) \text{ (eV}^{-1}\text{cm}^{-3}\text{)}$	$N(E_F) \text{ (eV}^{-1}\text{cm}^{-3}\text{)}$
NAN1	23.80		2.094×10^{27}	2.446×10^{22}
NAN3	23.29		2.106×10^{33}	5.666×10^{22}
NAN7	23.80		9.480×10^{29}	4.975×10^{26}

Activation energy of all the three films is of the same size approximately. This means that interfacial layer thickness does not affect significantly the activation of conduction process.

3.2.2. Resistivity variation of NAN2, NAN4, NAN5, NAN6, NAN8, NAN9 and NAN10 films.

The films NAN2, NAN4, NAN5, NAN6, NAN8, NAN9 and NAN10 showed Metal to Semiconductor transition (MST). Of these, NAN4 and NAN5 films have exhibited extended tails on either sides of the transition temperature. Hence, these films have been considered separately for analysis. Other films which have got only short tails on semiconducting side have been considered for analysis under one group. Resistance varied linearly with temperature for NAN2, NAN6, NAN8, NAN9 and NAN10 films for temperature above 150K (Fig.6). Temperature coefficient of resistance $TCR = (dp/dT)/\rho_{300K}$ has been determined and recorded in Table.4. TCR values are positive and are of the order 10^{-4} K^{-1} .

Table 4: Temperature coefficient of resistance, TCR of NAN2, NAN6, NAN8, NAN9 and NAN10 films.

Films $\rightarrow$	NAN2	NAN6	NAN8	NAN9	NAN10
$TCR \times 10^{-4} \text{ (K)}^{-1} \rightarrow$	1.050	2.323	1.307	1.644	1.755

Further, linear variation of resistivity with temperature above 150 K is in agreement with Matheissen's rule. According to Matheissen's rule, at high temperature electron-phonon interaction dominates over electron-electron and electron-impurity scattering. Then, resistivity varies linearly with temperature. For $T < 150K$, several attempts have been made to fit the data to $\rho = AT^5$, as dedicated by Matheissen's rule and also to Arrhenius expression $\rho = \rho_0 \exp(E/K_B T)$. But no good fits were achieved, implying that for these films, different theoretical treatment is required to understand resistivity below 150 K.

3.2.3. Resistivity variation of NAN4 and NAN5 films

The $\rho(T)$ data on NAN4 and NAN5 films hints at the presence of competing mechanisms operating in these samples. The negative temperature coefficient of resistance (TCR) below T_C indicates localization of electrons and the positive TCR above T_C suggests delocalization of electrons [26]. The delocalization of electrons leads to metallic conductivity, which is a characteristic feature of degenerate semiconductor [27]. The metal-semiconductor transition can be explained using a view proposed for conduction in disordered matter [28] where, the minima in the $\rho(T)$ curve has been accounted for quantum correction (QC) terms in the conductivity expression. This view was developed based on Boltzmann semiclassical approach. The QC terms come from weak localization and Coulomb interaction effects that are related to structural disorder [28]. The localization effects have already been considered to interpret the MST observed in various oxides such as RuO_2 [29], ZnO:Ga [26] and undoped ZnO [30]. According to Lee and Ramakrishnan [28], the resistivity including the QC can be expressed as,

$$\rho = 1 / (\sigma_0 + a_1 T^{P/2} + a_2 T^{1/2}) + (bT^2) \quad (4)$$

Here, $\rho_0 (= 1/\sigma_0)$ is the residual resistivity. The second term in the denominator corresponds to weak localization and the third term corresponds to Coulomb interaction effects. The Eq.(4) was fit to the data of NAN4 and NAN5 as shown in Fig.7. The best fit parameters obtained are recorded in Table.5. From the Table.5, it can be seen that in case of NAN4, $a_1 > a_2$ and in the case of NAN5, $a_1 < a_2$. These indicate that within QC, weak localization effect dominates over coulomb interaction in NAN4 film and reverse is the case in NAN5 film. The values of P for NAN4 and NAN5 were determined to be 0.5 and 1.8 respectively, which correspond to electron-phonon interaction at weak localization sites [27].

Tables should be explanatory enough to be understandable without any text reference. Double spacing should be maintained throughout the table, including table headings and footnotes. Table headings should be placed above the table. Footnotes should be placed below the table with superscript lowercase letters. Sample table format is given below.

Table 5: Values of the fit parameters of Eq. (4) to the $\rho(T)$ data on NAN4 and NAN5 films.

Sample	$\sigma_0 (\Omega m)^{-1}$	a_1	P	a_2	b
NAN4	1.14×10^{-8}	33.5	0.5	1.62	1.67×10^{-7}
NAN5	1.23×10^{-8}	1.2	1.8	8.00	1.61×10^{-6}

*Moisture content on oven dry weight basis

Each figure should have a caption. The caption should be concise and typed separately, not on the figure area. Figures should be self-explanatory. Information presented in the figure should not be repeated in the table. All symbols and abbreviations used in the illustrations should be defined clearly. Figure legends should be given below the figures.] A sample figure is given in figure 1.

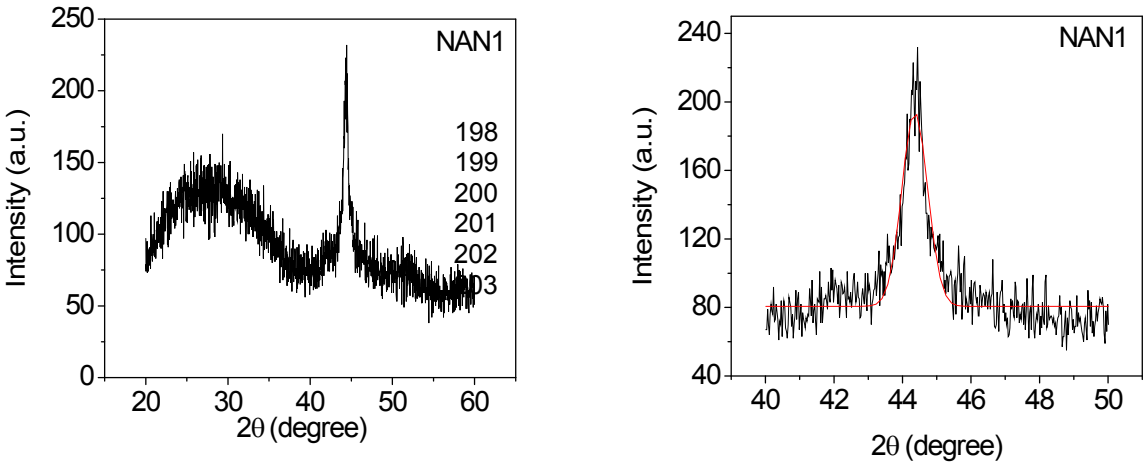


Fig.1. (a) XRD spectra for NAN1 film and (b) spectra around the peak position. The solid line is a Gaussian fit to the peak.

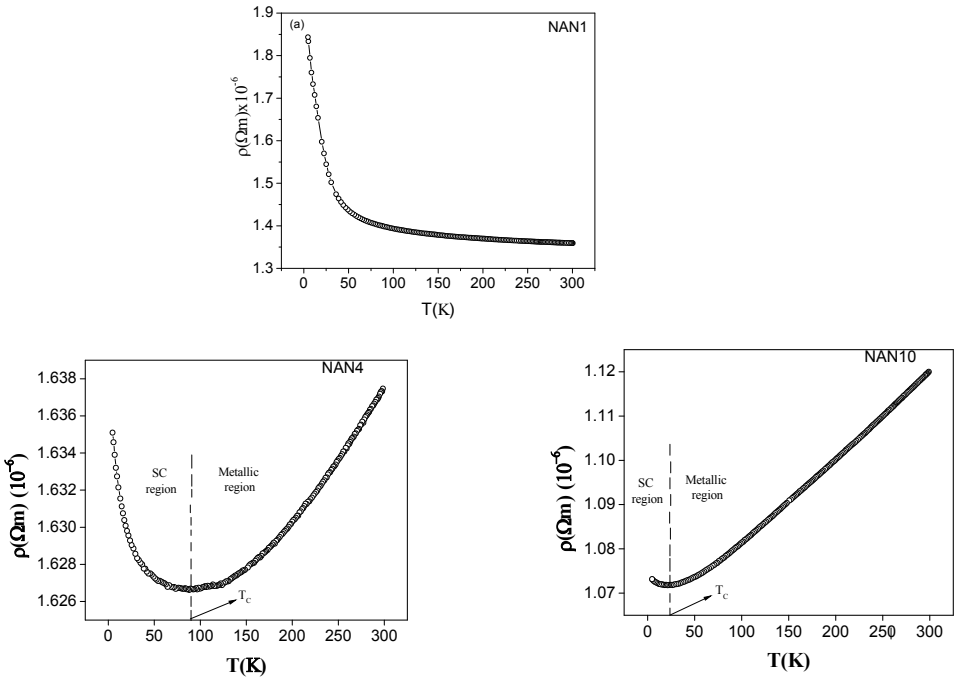


Fig.2: Temperature variation of resistivity of NAN1, NAN4 and NAN10

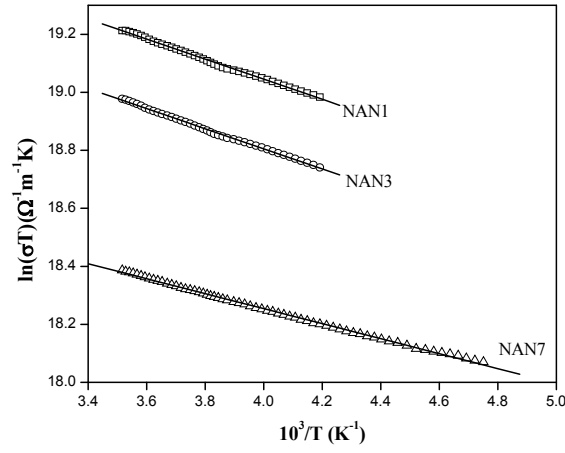


Fig. 3: The plots of $\ln(\sigma T)$ versus $(1/T)$ for NAN1, NAN3 and NAN7 films for $T > \theta_D$. Solid lines shown are the linear fits to the data.


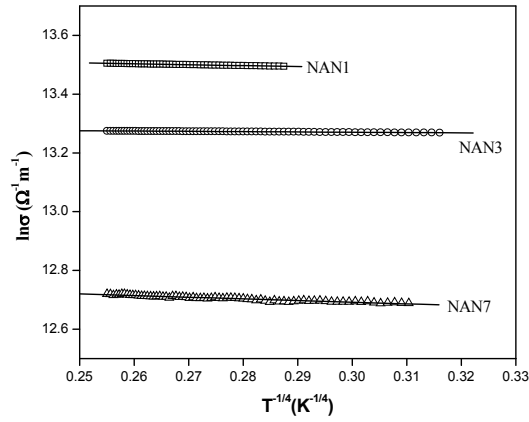


Fig. 4: Plots of $\ln(\sigma)$ versus $T^{-1/4}$ for NAN1, NAN3 and NAN7 films as per Mott's VRH model. Solid lines shown are the linear fits for $T < (\theta_D)$.

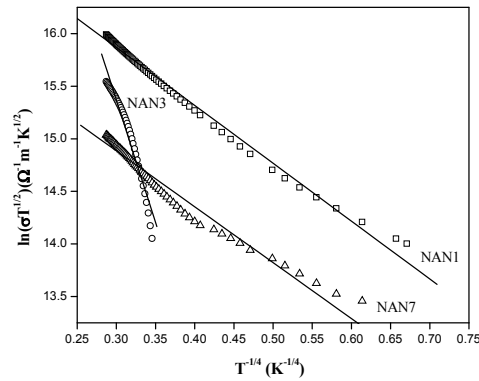

288
289
290
291
292
293
294
295
296
297
298
299
300
301
302
303
304
305
306
307
308
309
310
311
312
313
314
315
316
317
318
319
320
321
322
323
324
325
326
327
328
329
330
331
332
333
334
335
336
337
338
339
340
341

Fig.5 : The plots of $\ln(\sigma T^{1/2})$ versus $T^{-1/4}$ for the films as per Greaves VRH model. Solid lines shown are the liner fits to the data.

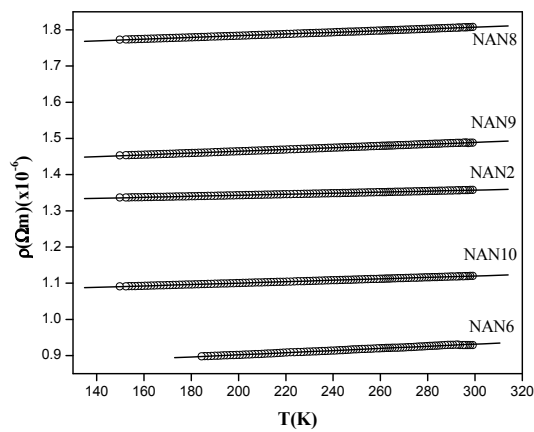


Fig.6: Plots of ρ vs T for NAN2, NAN6, NAN8, NAN9 and NAN10 films for $T > 150K$. The lines drawn are the linear fits to the data as per Matheissen's rule.

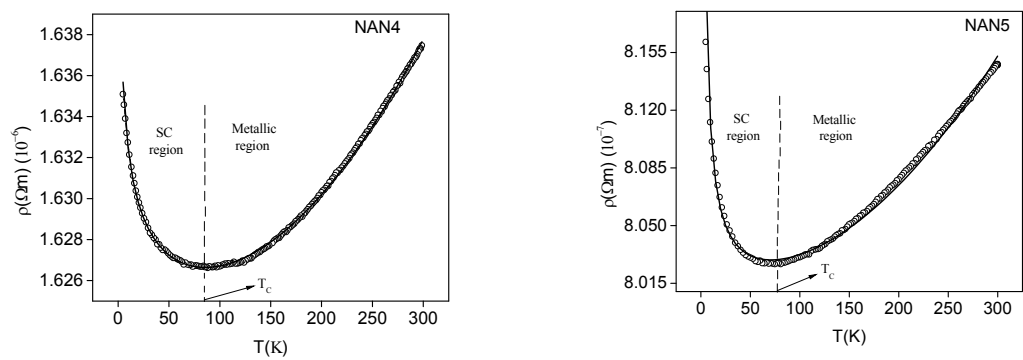


Fig.7: ρ versus T for NAN4 and NAN5 films. Solid lines are the best fits to Eq.(4).

4. CONCLUSION

- i). A set of sandwich films, $Ni(100\text{ nm})/Al(t)/Ni(200\text{ nm})$; $t=10\text{ nm}$ to 10 nm were deposited by thermal and electron beam gun methods at 473 K under high vacuum conditions. The structure and grain sizes were probed through X-ray diffraction (XRD) studies.
- ii) Low temperature electrical resistivity has been measured. Temperature dependence of resistivity showed complete semiconducting behavior for the films NAN1, NAN3 and NAN7. The data of these films has been analyzed in the light of Mott's small polaron hopping model and variable range hopping models due to Mott and Greave.
- iii) Resistivity data of NAN2, NAN6, NAN8, NAN9 and NAN10 films obeyed Matheissen's rule of linear relation between ρ and T at high temperature.

iv) Data on NAN4 and NAN5 films has been fit to resistivity expression which incorporates quantum correction in to it. The best fits were achieved and the coefficients corresponding to electron localization and coulomb interaction effects have been determined.

It is for the first time that sandwiched films of the present type have been found to be exhibiting MST and the data has been thoroughly analyzed taking various effects into account.

REFERENCES

1. Kowalewski M, Heinrich B, Cochran JF, Schurer P. J. 1997, Studies of interlayer exchange coupling in Fe/Cu/Fe ultrathin heterostructures, Appl Phys, 8:3904-3906.
2. Jonson MT, Purcell ST, McGee NWE, Coehoorn R, aan de Stegge J, Hoving W. 1992, Structural dependence of the oscillatory exchange interaction across Cu layers. Phys Rev Lett, 68:2688-2691.
3. Egelhoff Jr WF, Kief MT. 1992, Antiferromagnetic coupling in Fe/Cu/Fe and Co/Cu/Co multilayers on Cu(111). Phys Rev B condense Matter. 45:7795-7804.
4. Heinrich B, Celinski Z, Cochran JF, Arrott AS, Murtle K. 1993, Bilinear and biquadratic exchange coupling in bcc Fe/Cu/Fe trilayers: Ferromagnetic-resonance and surface magneto-optical Kerr-effect studies. Phys. Rev. B. 47:5077-5089.
5. Egelhoff Jr WF, Kef MT. Fe/Cu/Fe and Co/Cu/Co Multilayers on Cu (111): The absence of Oscillatory Antiferromagnetic Coupling. 1992. IEEE Trans Magnetics;28:5.
6. Kumar Dileep, Gupta Ajay. 2005. Effects of interface Roughness on Interlayer Coupling in Fe/Cr/Fe Structure. Hyperfine Interactions, 160:165-72.
7. Kholin DI, Drovoskov AB, Demokritov SO, Rickart M, Kreines NM. 2006. Noncollinear Interlayer Exchange in Fe/Cr/Fe Magnetic Structures with different Interface Roughness. Phys Metals Metallography. 101: S67-S69.
8. Botana J, Pereiro M, Baldomir D, Kobayashi H, Arias JE. 2008. Magnetic and Electronic Structure of nFe/3Cr/nFe slabs (n=1-6). Thin Solid Films ;516:5144-5149.
9. Aliev FG, Moshchalkov VV, Bruynseraede Y. 1998. Anomalous Low temperature of Metallic Trilayers-Possible Evidence for Electron-Scattering on Symmetrical 2-Level Systems. Phys Rev.B. 58 : 3625-3628.
10. Shamsutdinov NR, Bottger AJ, Tichelaar FD. 2006. The effect of Cu interlayers on grain size and stress in sputtered Fe-Cu multilayered thin films. Scripta Materialia. 54: 1727-1732.
11. El Khiraouia S, Sajieddinea M, Hehnb M, Robertb S, Lenobleb O, Bellouardb C, et al. 2008. Magnetic Studies of Fe/Cu Multilayers. Physica B .403:2509 - 2514.
12. Kumah DP, Cebollada A, Clavero C, Skuza JR, Lukaszew RA, Clarke R. 2007, Optimizing the planar structure of (1 1 1) Au/Co/Au trilayers. J Phys D Appl Phys. 40: 2699-2704.
13. Anil Singh, Sujeet Chaudhary, and D.K. Pandya, 2013. Hydrogen incorporation induced metal-semiconductor transition in ZnO:H thin films sputtered at room temperature Appl. Phys. Lett 102:172106.
14. P.J. Sadashivaiah, T. Sankarappa, T. Sujatha, et al. 2011. Magnetic and Low Temperature Conductivity Studies in Oxidised Nano Films J. Nano-Electron. Phys. 3, No4, 43-54.
15. A.W. Manjunath, T. Sankarappa, R. Ramanna et al. 2013. Low Temperature Electrical Resistivity Studies in Lead Thin Films. J. Nano-Electron. Phys. 5, 03026.
16. P.J. Sadashivaiah, T. Sankrappa, T. Sujatha, et al. 2010. Structural, Magnetic and Electrical Properties of Fe/Cu/Fe. Vacuum 85: 466-473.
17. Cullity of X-ray BD. Elements diffraction. Massachusetts, USA: Addison-Wesley Inc.; 1956.
18. A. Hakim, J. Hossain, Khan. 2009. Temperature effect on the electrical properties of undoped Nio Thin Films. Renew, Energ. 34, 2625 - 2629.
19. S.A. Makhlof, 2008. Electrical Properties of Nio Films Obtained by High Temperature Oxidation of Nickel. Thin Solid Films. 516: 3112 - 3116.
20. S.A. Makhlof, M.A. Kaseem, A. Rahim, 2009. Particle size-dependent Electrical Properties of Nanocrystalline Nio. J. Matter. Sci. 44: 3438 - 3444.
21. N.F. Mott. 1968. Conduction in glasses containing Transition Metal ions. J. Non-Cryst. Solids 1, 1 - 17.

22. N.F.Mott, 1969. Conduction in non-crystalline materials. *Phil. Mag.* 19, 835-852.
23. G.N. Greaves. 1973. Small Polaron Conduction in $V_2O_5P_2O_5$ glasses. *J. Non-Cryst. Solids* 11, 427 – 446.
24. S.R. Elliot, *Physics of amorphous materials* (Longman London and New York: 1984
25. M.M. El-Desoky. 2003. Small Polaron Transport in V_2O_5 -Nio- TeO_2 Glasses. *J. Mater. Sci.-Mater. Electron.* 14, 215 – 221.
26. A. K. Pradhan, L. Douglas, H. Mustata, R. Mundle, D. Hunter, and C. E. Bonner. 2007. Pulsed-laser deposited Er:ZnO films for 1.54 μm emission. *Appl. Phys. Lett.* 90, 072108
27. K. Shimakawa, S. Narushima, H. Hosono, and H. Kawazoe. 1999. Electronic transport in degenerate amorphous oxide semiconductors *Philos. Mag. Lett.* 79, No.9. 755 -761.
28. P. A. Lee and T. V. Ramakrishnan. 1985. Methods of Quantum Field Theory in Statistical Physics. *Rev. Mod. Phys.* 57, 287.
29. G. Herranz, F. Sanchez, B. Martinez, J. Fontcuberta, M. V. Garcia-Cuenca, C. Ferrater, M. Varela, and P. Levy. 2004. Weak Localization effects in Some Metallic Pervoskites. *Eur. Phys. J. B* 40, 439–444.
30. M. Nistor, F. Gherendi, N. B. Mandache, C. Hebert, J. Perriere, and W. Seiler 2009. Metal-semiconductor transition in epitaxial ZnO thin films. *J. Appl. Phys.* 106, 103710.