

Structural and Optical Properties of Polymer Blend Nanocomposites Based on Poly (vinyl acetate-co-vinyl alcohol)/TiO₂ Nanoparticles

A. Ismaila¹, P. O. Akusu¹ and T. O. Ahmed^{2*}

¹Department of Physics, Ahmadu Bello University, Zaria, Nigeria

²Department of Physics, Federal University Lokoja, Kogi, Nigeria

Research Article

13

ABSTRACT

Titanium dioxide and organic polymer blend poly (vinyl acetate-co-vinyl alcohol) based nanocomposite membranes were prepared and their chemical structure, phase relationship and optical properties investigated. The Scanning Electron Microscopy (SEM) coupled with Energy Dispersive X-ray Spectroscopy (EDS) analysis reveals TiO₂ to be almost isomorphous ($\geq 99\%$ phase purity) with spherical particles having diameters in the range 25-40nm. The composites were characterized by Fourier Transform Infra Red (FTIR) Spectroscopy, SEM, X-Ray Diffraction (XRD) and Ultraviolet-visible (UV-vis) Spectrophotometry. The FTIR Spectroscopy reveals significant absorptions below 900cm⁻¹ to represent Titanium bonds with organic groups and Oxygen while other prominent functional groups above 900cm⁻¹ reflect the additivity of polyvinyl alcohol and polyvinyl acetate. It was found that embedding inorganic nanoparticles of TiO₂ into the polymer blend matrix of poly (vinyl acetate-co-vinyl alcohol) allowed for some crystallinity formation and cross-linking of the polymer composites during annealing. The XRD results show more defined peaks assigned to each phase of the composite as the TiO₂ content increases from 1 to 4% weight ratio, thus indicating that Nanoparticle filler remain in the semi-crystalline polymer matrix as a separate crystalline phase, which is in good agreement with the SEM. Finally, the resonant coupling between (UV-vis) light and the collective electronic transitions of polymer nanocomposites are examined using UV-vis Spectrophotometer. The variation in the percentage absorbance and transmittance over wavelength range 200nm-900nm is also attributed to TiO₂ Nanoparticles (Nps) content (1-4%) in the samples.

Keywords: Polymer blend; TiO₂ Nanoparticles; Polymer Nanocomposites; Chemical structure; UV-visible light absorber.

* Tel.:

E-mail address: tajahmol@yahoo.co.uk; tajahmol@gmail.com.

1. INTRODUCTION

In the last few years, the prospects for polymer blending have been compared to the alloying of metals because it requires little or no extra capital expenditure compared to the production of new polymers. This leverage has led to extensive use of polymer blends in the polymer industry over the last few years. Also, polymer blending offers the possibility of producing a range of polymeric materials with properties completely different from those of the blend constituents [1]. Blend properties are crucially affected by phase morphology and this in turn depends upon a number of factors including the choice of parent polymers, compatibilizers, blend composition, moisture content and the method of blend preparation [2,3]. Because of the significant interest in interfacial interaction between inorganic and organic phases (such as variety of polymer and their blend derivatives) as well as size-dependent phenomena of nanoscale particles, polymer blend nanocomposites are capable of dramatically improving numerous favorable properties without losing the inherent good properties of the polymer phases such as ductility, optical transparency etc. these advantages are never achieved in the conventional polymer composites. In addition, property enhancements in polymer nanocomposites are achieved at a very low loading (<5 wt %) of inorganic nanoparticles while the conventional polymer composites (polymer containing microparticles/micron-sized particles as fillers) usually require much loading of the order of 25-40 wt % [4].

In contrast to the traditional dyes, inorganic semiconductive nanocrystals have more resistant to chemical attacks and low degradation with higher photobleaching, broader excitation wavelength range, narrower and tunable emission spectra [5,6,7,8]. This influence has attracted an enormous research effort leading to a myriad of potential applications in engineering, medicine, biology, electronics and allied industries. Their optical properties have been the center of attraction due to strong size-dependent quantum confinement effect associated with inorganic semiconductive nanocrystals. For the development of novel nanodevices such as electronics and optical devices, various stabilizers (surfactants, polymers or coupling agents) have been employed to modify the surface functionalities of the nanocrystals [9,10], as these nanocrystals are seldom prepared without aggregation. A great deal of attention has been focused on TiO_2 in contrast to other semiconducting materials, because of its low cost, non-toxicity, chemical stability, resistance to photocorrosion, high photocatalytic activity and high refractive index [11,12]. In the last decade, most studies are mainly focused on the dispersion of nanocrystalline TiO_2 powder for photocatalysis compared to TiO_2 thin films due to its higher photocatalytic activity [13]. It is an established fact that a mixture of anatase TiO_2 and a small percentage of rutile TiO_2 give optimal photocatalytic efficiency as the anatase phase has a wider band gap of 3.20 eV [14].

Polymer nanocomposites represent a merger between traditional organic and nanosized inorganic materials, resulting in compositions that are truly hybrid. The key to forming such novel materials is adequate understanding and manipulation of the guest-host chemistry, occurring between the polymer and the nanoparticles, in order to obtain a homogenous dispersion and a good contact between polymer and added particle surfaces [15]. Generally, the resultant nanocomposites display enhanced favorable properties such as conductivity, toughness, optical activity, catalytic activity, chemical selectivity etc [16]. These attributes have led to the growing interest and uses in various fields such as military equipments, safety and protective garments, automotive, aerospace, electronic and optical devices. A lot of research works exploiting these aforementioned properties have been carried out for possible applications including flame retardancy, chemical resistance, UV resistance, electrical conductivity, environmental stability, water repellency, magnetic field resistance, radar absorption etc [17, 18, 19, 20, 21].

In this paper, we report the development of Poly (vinyl acetate-co-vinyl alcohol)/ TiO_2 nanocomposites achieved via a two-stage synthetic route and the relationship between

structural and optical properties of the resulting hybrid Poly(vinyl acetate-co-vinyl alcohol)/TiO₂ nanocomposites employing Fourier Transform Infrared (FTIR) spectroscopy, Scanning Electron Microscopy (SEM), X-Ray Diffraction (XRD) analysis and UV-visible Spectrophotometry.

2. MATERIAL AND METHODS

Poly (vinyl acetate-co-vinyl alcohol)/TiO₂ nanocomposites were produced via a two-stage reaction involving the synthesis of TiO₂ Nanoparticles (Nps) from titanium (IV) chloride {TiCl₄, BDH Limited Poole, England} employing hydrothermal technique and subsequent mixing of modified TiO₂ Nps with Poly(vinyl acetate-co-vinyl alcohol) dissolved in toluene via one-pot reaction. Surface morphology of the synthesized TiO₂ nanoparticles was observed using EVOI MA10 (ZEISS) multipurpose scanning electron microscope operating at 20kV employing secondary electron signals. Four samples of Poly (vinyl acetate-co-vinyl alcohol)/TiO₂ nanocomposites containing 1-4% of TiO₂ Nps were produced by solution casting into Petri dishes. The samples were oven dried at temperature lower than the melting point of the polymer blend for 12hrs and subsequently flat and uniform thin samples were obtained. The FTIR spectra of all the component reagents, polymer blend and the prepared nanocomposite samples were obtained using SHIMADZU FTIR-8400S Spectrophotometer in transmission mode without KBr. The spectra were recorded in the frequency range from 400 to 4600 cm⁻¹, after 25 scans, with resolution of 2cm⁻¹. The positions and intensities of the IR bands were processed with Spectral Analysis software.

Surface morphologies of Poly (vinyl acetate-co-vinyl alcohol)/TiO₂ nanocomposites were observed using EVOI MA10 (ZEISS) multipurpose scanning electron microscope operating at 20kV employing secondary electron signals at a magnification of 500X and the particle size distribution was obtained using imaging software (Image-J). The crystallinity of polymer blend/TiO₂ nanocomposites was observed using X-Ray Diffractometer (Phillips X'pert Pro X-Ray Diffractometre) employing a 1.54060Å copper X-ray source. The samples were scanned from 2θ = 5°-80° using a step size of 0.06°. The percentage crystallinity (X_c) was calculated following the procedure proposed by [22], with the Scientific Graphing and Data Analysis

Software (Origin 8.0), using the following equation:
$$X_c = \frac{A_c}{A_c + A_a}$$
 where X_c, (percentage crystallinity), is the ratio of crystalline peak area (A_c) to the sum of the crystalline peak area (A_c) and amorphous peak area (A_a). Finally, the absorption/filtering property of the polymer blend /TiO₂ nanocomposites was studied in the ultraviolet (UV) radiation wavelength range of 200nm-400nm and visible radiation wavelength range of 400nm-900nm using JENWAY 6405 UV-visible Spectrophotometer.

3. RESULTS AND DISCUSSION

The image presented in figure 1 together with the corresponding EDS spectra obtained using characteristic x-rays emitted by TiO₂ nanoparticles was observed at a magnification of 83.04kX. The uniform contrast in the image revealed TiO₂ to be almost isomorphous. Nevertheless, Oxygen and Nitrogen occur with minor concentrations as impurities thereby making Ti the dominant element with concentration of about 99.5% as depicted in the EDS spectra (fig 1b). The morphology of TiO₂ nanoparticles is such that the particles are closely packed and spherical in shape. The average diameter of the particles is in the range of 25-40nm reflecting that TiO₂ nanoparticles are transparent and suitable filler for polymer composite applications.

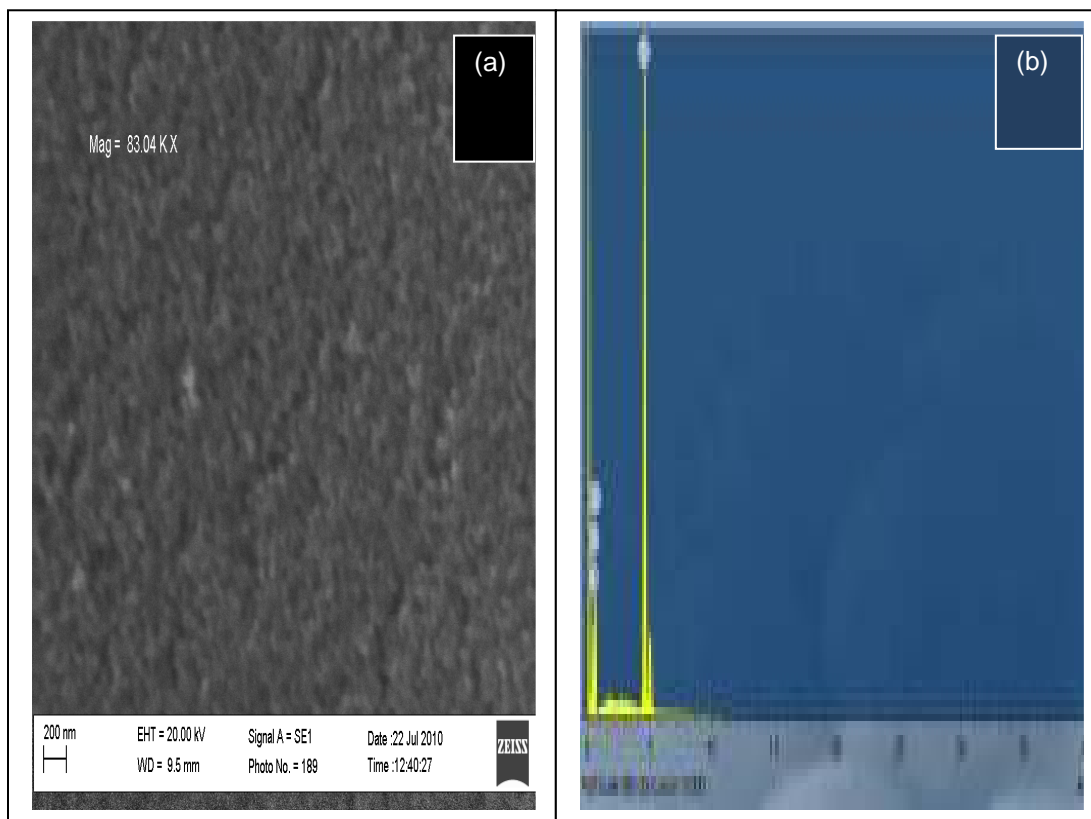


Figure 1: Microstructure and elemental composition of TiO₂ Nps: (a) SEM image of TiO₂ Nps (b) EDS spectra of TiO₂ Nps.

The spectra for the functionalized TiO₂ nanoparticles, poly (vinyl alcohol), poly (vinyl acetate), polymer blend [poly (vinyl acetate-co-vinyl alcohol)] and the functionalized TiO₂ are given in figure 2 (a-d) below. It is an established fact that the fundamental vibrations of solids (finger prints) are localized in the low frequency region ($<1200\text{cm}^{-1}$) of the midrange ($400\text{--}4000\text{cm}^{-1}$) of the infrared (IR) spectrum. Also, as reported by [23], the Ti-O bond is clearly located in the range from $400\text{--}900\text{cm}^{-1}$. In this work, the significant absorptions observed below 900cm^{-1} represent Ti bonds with vinyl groups, secondary alcohols, carbonyl groups and oxygen. The prominent functional groups in poly (vinyl alcohol), poly (vinyl acetate) and their blend are OH stretching vibrations, CH₂ stretching and bending vibrations, CH₃ bending vibrations, C-O-C vibration in esters, $\nu\text{C}=\text{O}$ stretching vibration, C-OH stretching vibrations, CH bending and C=O stretching vibration.

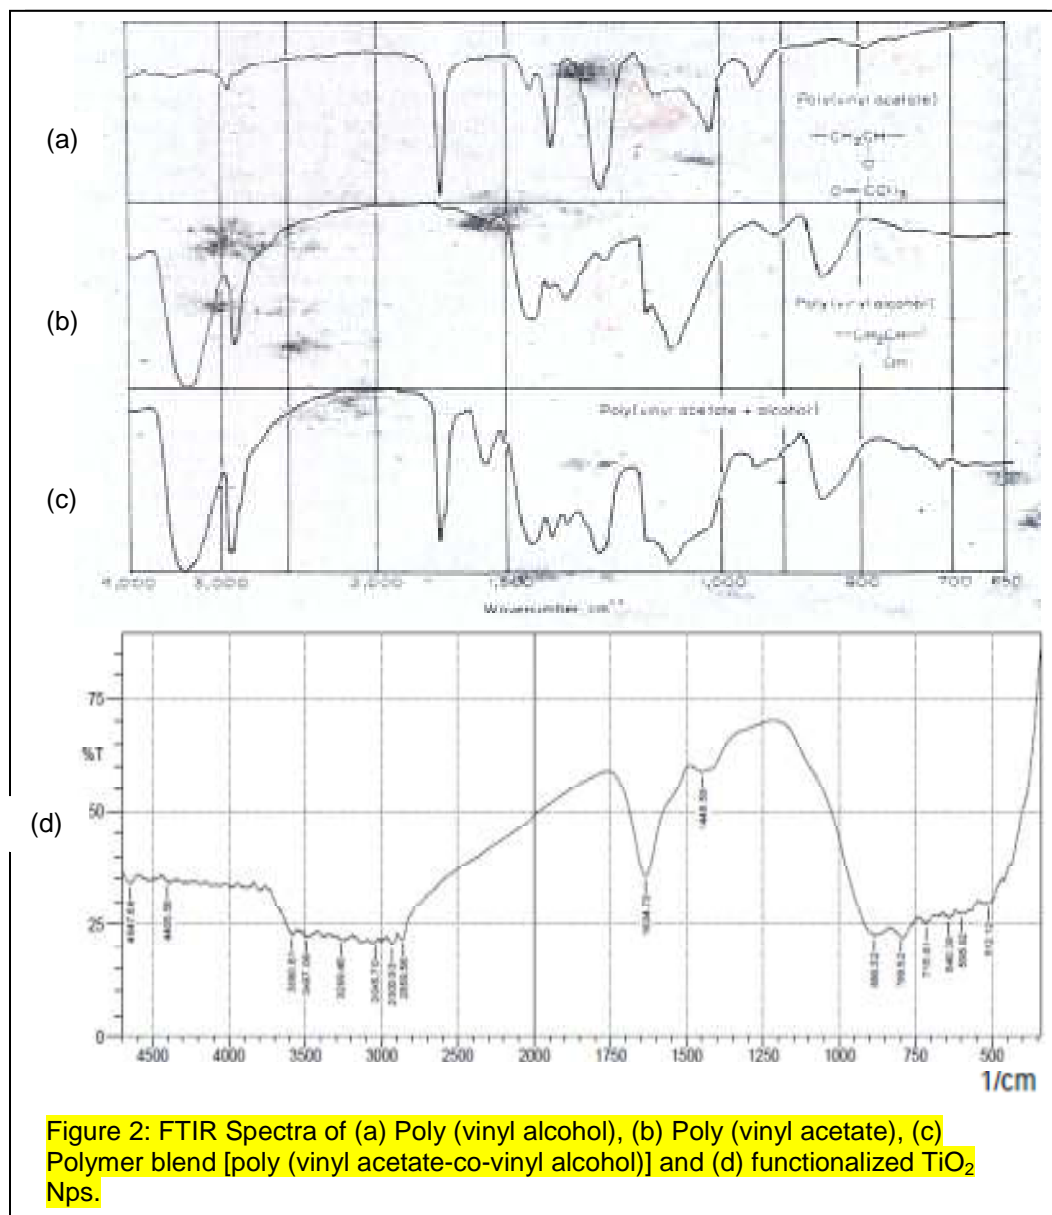


Figure 2: FTIR Spectra of (a) Poly (vinyl alcohol), (b) Poly (vinyl acetate), (c) Polymer blend [poly (vinyl acetate-co-vinyl alcohol)] and (d) functionalized TiO_2 Nps.

From figure 3(a-d), it can equally be deduced that the OH stretching vibrations of the intermolecular hydrogen bonding occurring in the range 3427.62cm^{-1} - 3483.56cm^{-1} is basically due to the adsorbed H-O-H. Organics (methylene groups) are also represented by the $\nu_{\text{as}}\text{-CH}_2$ asymmetrical stretching vibrations in ranges slightly above 2910cm^{-1} . The CH stretching vibrations with coexisting terminal triple bonds resulting from remnant alkynes occur in the range 2067.76cm^{-1} - 2145.88cm^{-1} . All the changes observed in the vibration frequency of $\nu\text{C=O}$ in the blend indicates that the incorporation of the nanofillers (TiO_2) has great influence on the vibration frequency of $\nu\text{C=O}$. Furthermore, conjugation with CH_3 (phenyl groups) results in an increase in bond length of C=O thereby creating functional sites on the surface of the polymer blend. The C-O-C vibrations in esters occurring in the frequency ranges 949.01cm^{-1} - 950.94cm^{-1} and 1284.63cm^{-1} - 1293.31cm^{-1} represent the

possible combination of acetate and alcohol groups. Finally, the functional groups appearing in the range 383.85cm^{-1} - 491.66cm^{-1} represent Ti-O bonds of the functionalized TiO_2 nanoparticles. The observed spectra of the polymer-blend/ TiO_2 nanocomposites reveal the additivity of the spectra of polyvinyl alcohol and poly vinyl acetate with the modified TiO_2 Nps. In figures 3(a) and 3(b), most of the functional groups peculiar to the component reagents were observed but in figures 3(c) and 3(d), chemical reactions between the component reagents and the increase in the concentration of the functionalized TiO_2 nanoparticles from 2%-4% are responsible for the extinction of the functional groups as a result of oxidation and hydrolysis.

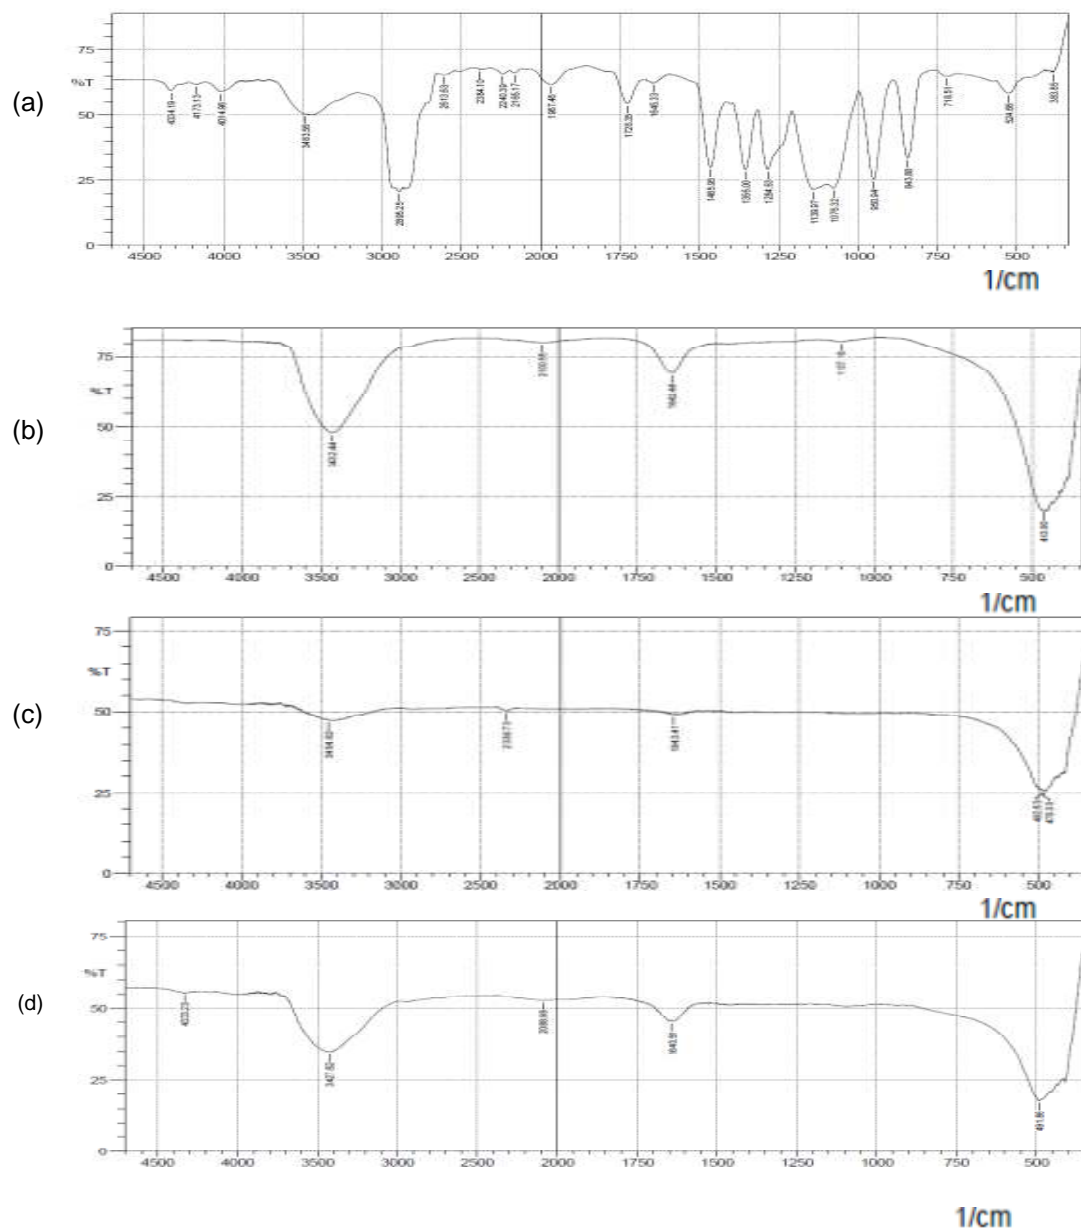


Figure 3: FTIR Spectra of Polymer blend/ TiO_2 Nanocomposites containing:
(a) 1% of TiO_2 Nps (b) 2% of TiO_2 Nps (c) 3% of TiO_2 Nps and (d) 4% of TiO_2 Nps.

The uneven baseline in the XRD patterns seen in figure 4 (a-d) for all the samples is due to the large amount of amorphous polymer content. The addition of TiO₂ nanoparticles to the polymer blends improved the crystallinity of the composites. The diffraction peaks in the range $2\theta = 15^\circ$ - 20° can be linked to crystalline behaviour of the polymer blends. The peaks at $2\theta = 19.66^\circ$, 19.84° , 20.34° , and 20.49° with d-spacings $d = 4.5154\text{\AA}$, 4.4742\AA , 4.3642\AA and 4.3325\AA indicate the presence of crystalline structure of PVA, consistent with the works of [24, 25]. Furthermore, the XRD patterns of polymer blend/TiO₂ nanocomposites reveal the presence of TiO₂ phase but few peaks representing TiO₂ phase have been shifted slightly to lower 2θ values ($2\theta = 21.91^\circ$, 22.13° , 22.37° , 22.45° , 22.78° , 22.80° and 22.99°) due to slight expansion of TiO₂ crystal structure as a result of surface modification and bonding with the polymer blend matrix. This is also consistent with the results presented in some literatures [26, 27]. The average crystallite size corresponding to structural order of the pattern determined from integral breadth of the peaks according to Scherrer's equation [28] have values ranging from $1688 \pm 290\text{nm}$ to $4589 \pm 130\text{nm}$. The percentage crystallinity values of the polymer blend/TiO₂ nanocomposites following the procedure proposed by [22] range from $56.9 \pm 0.2\%$ to $67.6 \pm 0.7\%$. The sample with 4% TiO₂ content displayed higher percentage crystallinity compared to other samples.

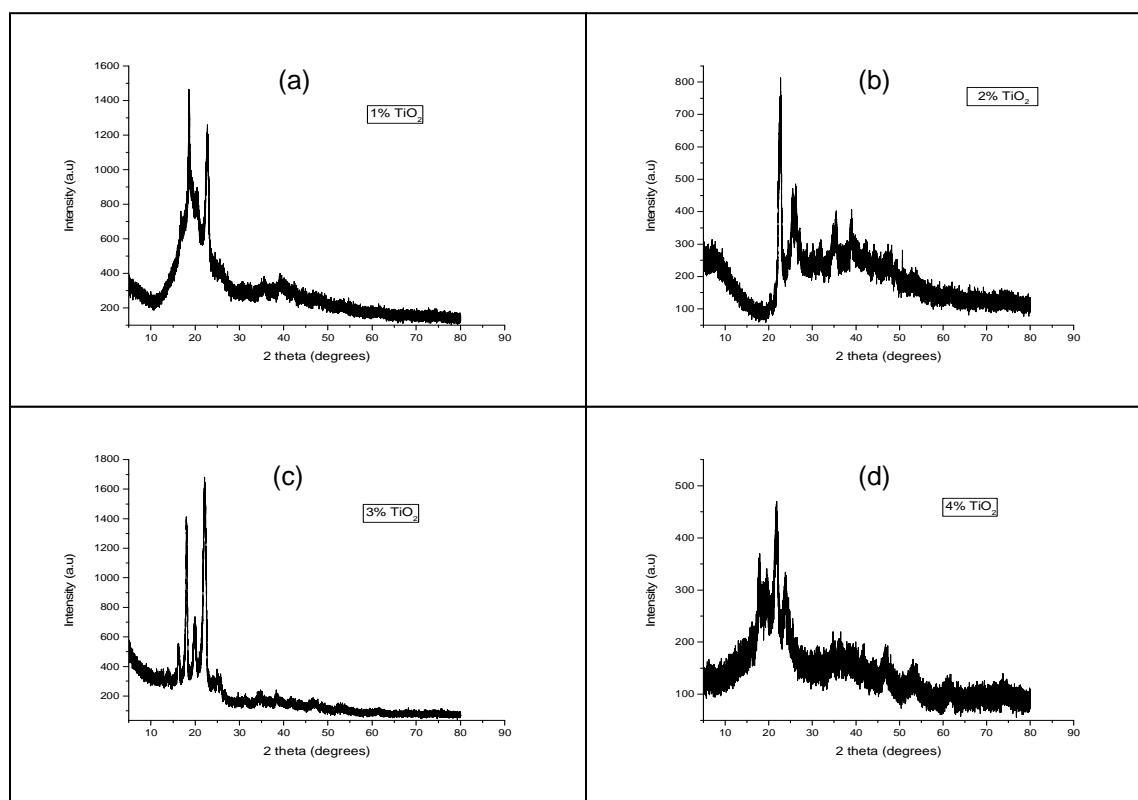


Figure 4: X-ray Diffraction Patterns of Polymer Blend/TiO₂ Nanocomposites containing (a) 1% of TiO₂, (b) 2% of TiO₂, (c) 3% of TiO₂ and (d) 4% of TiO₂.

The microstructure of the polymer blend/TiO₂ nanocomposites reveals two distinct phases comprising of lighter modified TiO₂ nanoparticles and dark bulk polymer blend matrix. The lighter modified TiO₂ nanoparticles are evenly dispersed over the dark bulk polymer matrix with spherical shapes and the concentration increased with increasing content of the

modified TiO₂ NPs (1%-4%) as depicted in figure 5(a-d). The contrast observed in the SEM images [figure 5(a-d)] arises from atomic number difference, since phases within a material are dependent upon back scattered electron yield and the corresponding atomic number of atoms present within different phases. As such, the modified TiO₂ nanoparticles appear lighter compared to the bulk polymer blend matrix because the atoms present in TiO₂ phase have higher atomic numbers and higher back scattered electron yield. The average particle diameters of the polymer-blend/TiO₂ nanocomposites as determined from SEM images using imaging software (Image J) range from 119±5µm to 179±4µm.

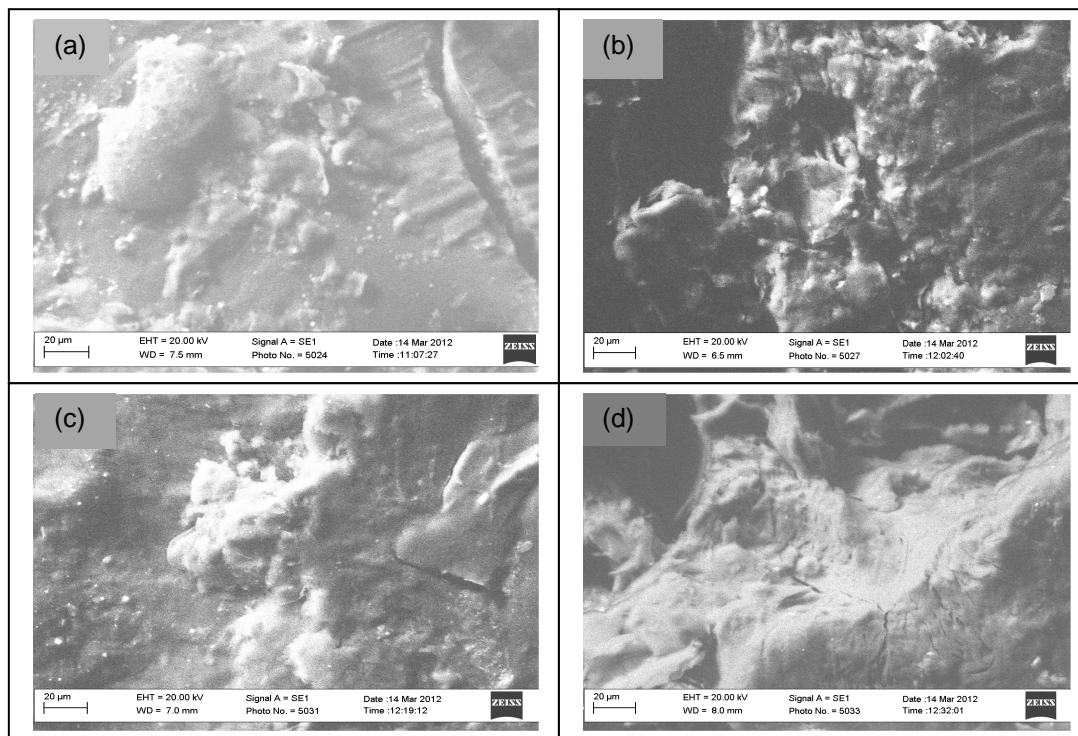



Figure 5: SEM Images of Polymer Blend/TiO₂ Nanocomposites containing: (a) 1% of TiO₂, (b) 2% of TiO₂, (c) 3% of TiO₂ and (d) 4% of TiO₂

It is a well known fact that changes occur when atoms or impurities are incorporated into a pure matrix (polymer, semiconductor, metal etc), because their environment is neither inert nor isotropic. Subsequently, exposing the anisotropic matrix (polymer nanocomposites) to UV-vis light may lead to resonant coupling between the photons (in this case, UV-vis component of the electromagnetic spectrum) and the collective modes (electronic transitions/excitations) of the polymer nanocomposites. The interaction of the UV-visible light with the polymer nanocomposites possibly will give rise to polarization of the nanocomposite matrix, which in turn can be seen as variation in the magnitude of absorption/transmission with respect to changes in wavelengths (i.e. 200-900nm) when examined using UV-vis spectrophotometer. In addition to this, anisotropy of the nanocomposite matrix resulting from addition of TiO₂ nanoparticles gave rise to varied properties as a result of slight structural modifications. The slight variation in the percentage absorbance over wavelength range (i.e. 200-900nm) is attributed to the TiO₂ nanoparticles content (1-4%) in each sample.

The UV-VIS spectra of polymer blend/TiO₂ nanocomposites are given in figure 6(a-d) below. The plot for polymer blend/TiO₂ sample (containing 1 wt % of nanoparticles) is presented in figure 6(a). The sample filters at the onset of ultraviolet radiation wavelength through 295nm above which it absorbs significantly and rapidly until maximum absorbance of 1.4% is recorded at a wavelength of 390nm. Slightly above the visible range, there is little decline in

absorbance but appreciates reasonably through the whole range with maximum recorded at a wavelength of approximately 500nm. The sample displayed excellent property of being an ultraviolet radiation filter at low wavelengths (<300nm) and absorber at higher wavelengths (300-400nm) of the UV range in addition to being an excellent visible absorber. Figure 6(b) portrays the behaviour for polymer blend sample containing 2 wt % of TiO₂ nanofillers. The spectrum shows absolute transparency from the onset of ultraviolet radiation wavelength range through a visible wavelength of 515nm. A much significant absorbance of approximately 3.0%, the maximum, is recorded slightly above that (i.e. at 520nm) from which the absorbance decreases very slightly with a minimum of 2.7% at 800nm. This material is an excellent UV filter and a very good visible radiation absorber.

A similar behaviour to the polymer blend samples described above is observed in both the remaining blend samples (with 3 wt % and 4 wt % of TiO₂ nanofillers respectively) as depicted in figures 6(c) and 6(d). However, there are slight shifts in the onsets of absorption, with the sample containing 3 wt % of TiO₂ having onset at a wavelength of 590nm corresponding to maximum absorbance of approximately 3.0% and that containing 4 wt % of TiO₂ having onset at 550nm corresponding to maximum absorbance of 2.9% as well. The minimum absorbance for these samples are recorded at 795nm (2.8%) and at 780nm (2.7%) respectively. These shifts are attributed to higher content of TiO₂ nanofillers in the polymer blends as TiO₂ are transparent to UV-vis light.

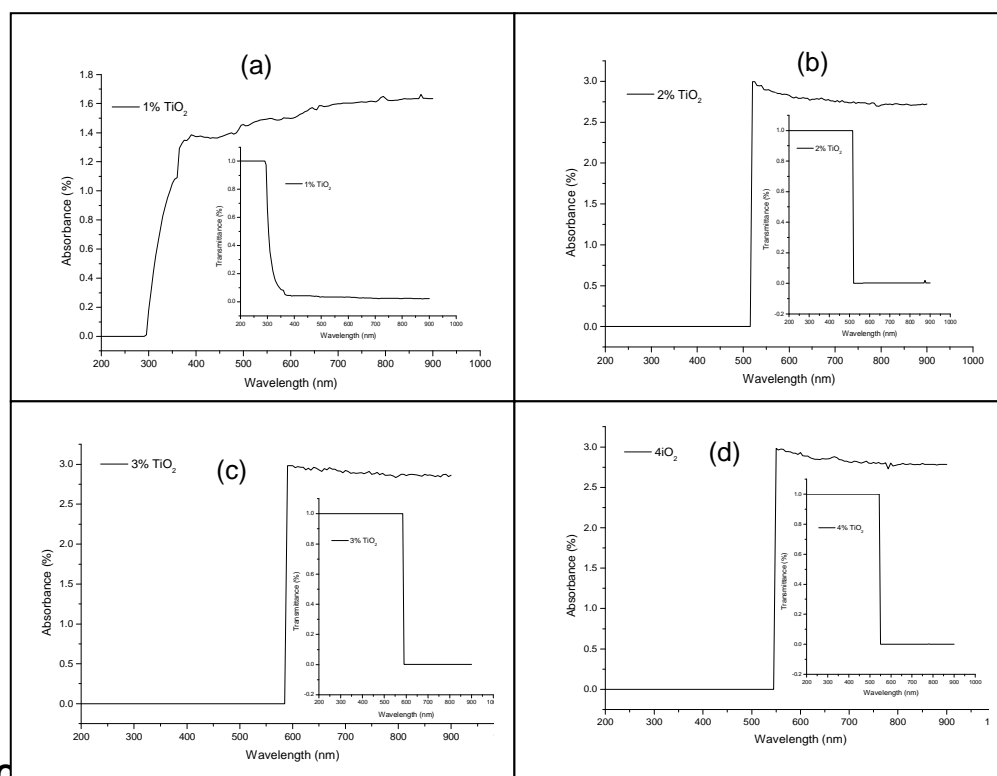

4. CONCLUSION

Figure 6: UV-vis spectra of Polymer-Blend/TiO₂ Nanocomposites containing: (a) 1% of TiO₂, (b) 2% of TiO₂, (c) 3% of TiO₂ and (d) 4% of TiO₂.

polymer blend matrices. FTIR spectroscopy proved the existence of covalent chemical bonding between the polymer chains and inorganic phase in the polymer blend nanocomposites. Thus, revealing significant absorptions below 900cm⁻¹ to represent titanium bonds with organic groups and oxygen while other prominent functional groups above 900cm⁻¹ reflect the additivity of polyvinyl acetate and polyvinyl alcohol. X-ray diffraction analysis of the polymer blend nanocomposites revealed an increase in the percentage

crystallinity from $56.9 \pm 0.2\%$ to $67.6 \pm 0.7\%$ for the polymer-blend nanocomposites as TiO_2 nanoparticles content increases from 1% to 4%. Observations from SEM analysis showed that the dispersion of TiO_2 nanoparticles in the polymer matrix was relatively uniform with particles having good adhesion with polymer domains. Investigation with UV-visible spectrophotometer revealed that the dispersion of TiO_2 nanoparticles improved the optical properties of the polymer blends. The fact that nanocomposites displayed some level of transparency at lower wavelengths indicates that the nanoparticles are not agglomerated. In addition, strong UV absorption in some of the nanocomposite samples was observed because of the incorporated TiO_2 particles. In fact, with the exception of sample with 1% content of nanoparticles, all the samples transmit UV radiation and absorb visible radiation at wavelengths of 520nm, 590nm and 550nm respectively. Thus the developed polymer blend nanocomposites could act as an efficient optically transparent UV filter and visible radiation absorber.

ACKNOWLEDGEMENTS

We thank Physics Advanced Laboratory, Sheda Science and Technology Complex, Abuja, Nigeria, National Research Institute for Chemical Technology, Zaria, Nigeria and the Multi-users Laboratory, Department of Chemistry, Ahmadu Bello University, Zaria, Nigeria for technical assistance during the experimental characterization.

COMPETING INTERESTS

Authors have declared that no competing interests exist.

AUTHORS' CONTRIBUTIONS

This work was carried out in collaboration between all authors. Authors TOA and POA designed the study. Author TOA wrote the protocol and wrote the first draft while, author TOA and author IA carried out the experimental work and analyses. Author TOA and author IA managed the literature searches. All authors read and approved the final manuscript.

REFERENCES

1. Wanchoo RK, Sharma PK. Viscometric Study on the Compatibility of some Water Soluble Polymer-Polymer Mixtures. Euro. Polym. J. 2003; 39: 1481-82.
2. Dyson RW. Engineering Polymers. Chapman and Hall, New York. 1990: 20-28
3. Chuu MS, Meyers RR. Effect of Moisture content on the dielectric behaviour of Poly (vinyl acetate)-Natural Rubber blend. J Appl Polym Sci. 1987; 34 (4):1447
4. Saujanya C, Radhakrishna S. Polymer Nanocomposites, J. of Polym. Sci. 2001: 42: 6723-6731.
5. Riegler J, Ditengou F, Palme K, Nann T. Blue Shift of CdSe/ZnS Nanocrystals-Labels upon DNA-Hybridization. J. Nanobiotechnol. 2008; 6(1): 7.

- 375 6. Bruchez Jr. M, Moronne M, Gin P, Weiss S, Alivisatos AP. Semiconductor
376 Nanocrystals as Fluorescent Biological labels. *Science*. 1998: 281(5385):2013–
377 2016.
- 378 7. Chan WCW, Nie S. Quantum Dot Bioconjugates for Ultrasensitive Nonisotopic
379 Detection *Science*. 1998: 281(5385): 2016–2018.
- 380 8. Jaiswal J, Mattoussi H, Mauro J, Simon S. Long-term multiple Color Imaging of Live
381 Cells Using Quantum Dot Bioconjugates. *Nat. Biotechnol.* 2003: 21(1): 47–51.
- 382 9. Patra MK, Manoth M, Singh VK, Gowd GS, Choudhry VS, Vadera SR, Kumar N.
383 Synthesis of Stable Dispersion of ZnO Quantum Dots in Aqueous Medium Showing
384 visible Emission from Bluish-Green to Yellow. *J. Lumin.* 2009: 129 (3):320–324.
- 385 10. Guo Z, Kumar C, Henry LL, Domes EE, Hormes J, Podlaha EJ. Displacement
386 Synthesis of Cu Shells Surrounding Co Nanoparticles. *J. Electrochem. Soc.* 2005:
387 152(1): D1–D5.
- 388 11. Legrini O, Oliveros E, Braun AM, Photochemical Processes for Water Treatment.
389 *Chem. Rev.* 1993: 93(2): 671-698.
- 390 12. Sugimoto T, Zhou X, Muramatsu A. Synthesis of Uniform Anatase TiO₂
391 Nanoparticles by Gel-Sol Method: 3. Formation Process & Size Control. *J. Colloid*
392 *Interface Sci.* 2003: 259(1): 43-52.
- 393 13. Jiaguo Y, Jimmy CYU, Cheng B, Zhao X. Photocatalytic Activity & Characterization
394 of the Sol-Gel Derived Pb-Doped TiO₂ Thin-films *J. Sol-Gel Sci. Tech.* 2002: 24(1)
395 39-48.
- 396 14. Bouras P, Stathatos E, Lianos P. Pure versus Metal-ion-doped Nanocrystalline
397 Titania for Photocatalysis. *Appl. Catal. B: Environ.* 2007: 73(1-2): 51-59.
- 398 15. Lagashetty A, Venkataramen I. *Polymer Nanocomposites*. John Wiley and sons.
399 2005.
- 400 16. Garcia C, Maria M, Dela L. *Polymer-Inorganic Nanocomposites: Influence of*
401 *Colloidal Silica*, A PhD thesis submitted to the university of Twente, Netherlands.
402 2004.
- 403 17. Mohan S, Lauren NC, Surya SG, Karen IW. Melt Intercalation of Polystyrene in
404 Layered Silicates, *J. of Polym. Sci.: part B: Polym. Physics*. 1996: 34: 1433-1449.
- 405 18. Lee SS, Lee CS, Kim MH, Kwak SY, Park M, Lim S, Choe CR, Kim J. Specific
406 Interaction Governing the Melt Intercalation of Clay with Poly(styrene-co-
407 acrylonitrile) Copolymers. *J. of Polym. Sci.: part B: Polym. Physics*. 2001: 39: 2430-
408 2435.
- 409 19. Pegoretti A, Dorigato A, Penati A. A Tensile Mechanical Response of Polyethylene-
410 Clay Nanocomposites. *Express Polymer Letters*. 2007: 1(3): 123-131.
- 411 20. Tolstov AL, Matyushov VF, Klymchok, DO. Synthesis and Characterization of Hybrid
412 Cured Poly (ether-urethane) Acrylate/Titania Microcomposites Formed from
413 Tetraalkoxytitanate Precursors, *Express Polymer Letters*. 2008: 2(6) 449-459.
- 414 21. Manias E, Zhang J, Huh JY. Polyethylene Nanocomposite Heat Sealants with a
415 Versatile Peelable Character, *Macromol. Rapid Commun.* 2009: 30: 17-23.

- 416 22. Eichhorn S J, Young RJ. The Young's modulus of Microcrystalline cellulose.
417 Cellulose. 2001: 8: 197-207.
- 418 23. Morterra C, Magnacca G. A case Study: Surface Chemistry & Structure of Catalytic
419 Aluminas as Studied by Vibrational Spectroscopy of Adsorbed species" Catal.Today.
420 1996: 27: (3-4): 497-532.
- 421 24. G'eminarda JC, Bonraya DH. Thermal Conductivity Associated with a Bead-Bead
422 Content Decorated by a Liquid Bridge; An Experimental Study Based on the
423 Response of a Chain Subjected to Thermal Cycles. Gayvallet Eur, Phys. 2005:
424 48: 509-517.
- 425 25. Lee GW, Park M, Kim J, Lee JI, Yoon HG. Enhanced thermal conductivity of
426 polymer Composites filled with hybrid filler. Composites Part A: Applied Science and
427 Manufacturing. 2006: 37: 727-734.
- 428 26. Shuqiang J, Hongmin Z. Electrolysis of Ti_2CO Solid Solution Prepared by TiC &
429 TiO_2 , Journal of Alloys & Compounds. 2007: 2007: 438: 243-246.
- 430 27. Yang Z, Choi D, Kerisit S, Rosso KM, Wang D, Zhang Z, Graffi G, Liu
431 J. Nanostructures and Lithium Electrochemical Reactivity of Lithium titanates and
432 Titanium oxides: A Review. Journal of Power Sources. 2009: 192(2): 588-598.
- 433 28. Patterson AL. The Scherrer formula for X-ray particle size determination. Physical
434 Review. 1939: 56(10): 978-982.

435

436

437

438

439

440

441

442

443

444

445

446

447

448

449